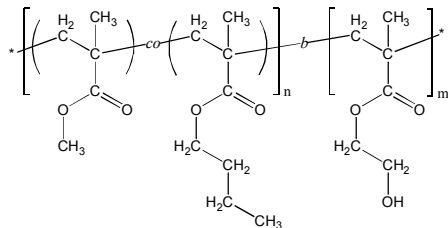


Sample Name:

**Poly(methyl methacrylate-*co*_(random)-n-butyl methacrylate)
-*block*-poly(2-hydroxyethyl methacrylate)**

Sample #: P10788-MMA_nBuMA_ran-b-HEMA**Structure:****Composition:**

$M_n \times 10^{-3}$ (g/mol)	23.0- <i>b</i> -28.0
M_w/M_n	1.20
Molar ratio MMA : nBuMA	47 : 53 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	17 : 28 : 55 (wt%)
T_g (MMA _n BuMA)	65 °C
T_g (HEMA)	112 °C

Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

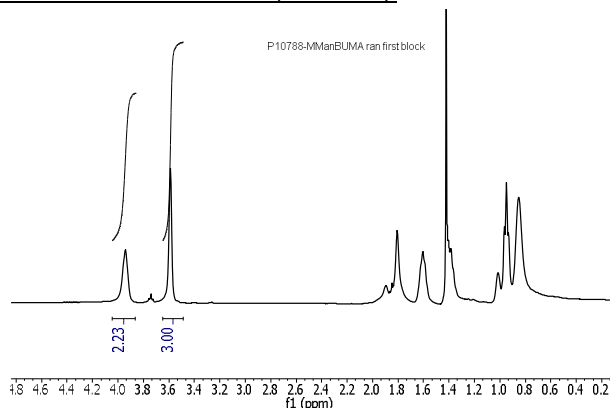
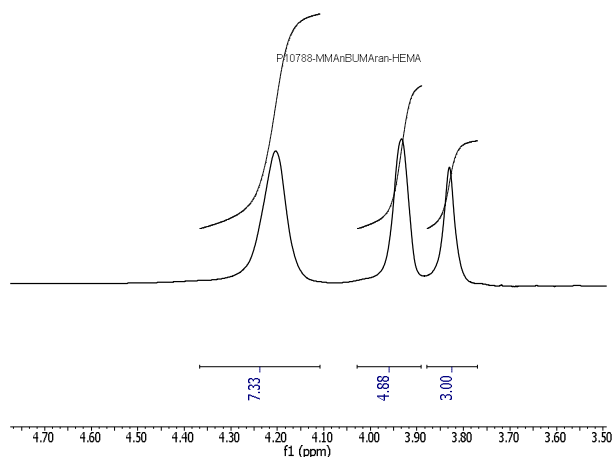
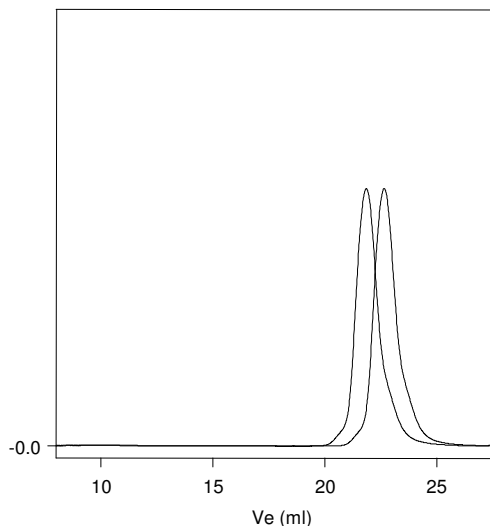
Solubility: The polymer is soluble in THF, DMF.

Characterization:

The polymer composition was determined by ¹H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the -OCH₂- protons of nBuMA (at δ = 3.9 ppm) to the integration of methoxy group of MMA (at δ = 3.6 ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of -OCH₂- protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA_nBuMA) block.

The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA_nBuMA-b-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.

¹H NMR of MMA_nBuMA_ran [first block]:**¹H NMR of MMA_nBuMA_ran-b-HEMA diblock copolymer:****SEC of MMA_nBuMA_ran and MMA_nBuMA_ran-b-HEMATMS:****P10788-MMA_nBuMA_ran-b-HEMA**

Size exclusion chromatography of

1. MMA_nBuMA ran block Mn 23,000 Mw: 26,500 Mw/Mn 1.15
2. MMA_nBuMA_ran-b-HEMATMS: 23,000-43,500 MW/Mn : 1.20

After deprotection Mn 23,000-*b*-28,000 Mw/Mn 1.20