


## Sample Name:

**Poly(methyl methacrylate-*co*(*random*)-*n*-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)**

## Sample #: P10792-MMA*n*BuMA*r*an-*b*-HEMA

### Structure:

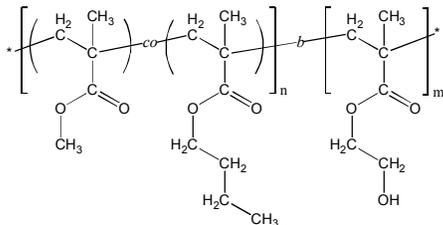

### Composition:

$M_n \times 10^3$ (g/mol)	28.0- <i>b</i> -35.0
$M_w/M_n$	1.25
Molar ratio MMA : nBuMA	50 : 50 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	18 : 26 : 56 (wt%)
$T_g$ (MMA <i>n</i> BuMA)	65 °C
$T_g$ (HEMA)	112 °C

### Synthesis Procedure:

Poly([methyl methacrylate-*co*-*n*-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and *n*-butyl methacrylate (*n*-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

**Solubility:** The polymer is soluble in THF, DMF.


### Characterization:

The polymer composition was determined by  $^1\text{H}$  NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the  $-\text{OCH}_2-$  protons of nBuMA (at  $\delta = 3.9$  ppm) to the integration of methoxy group of MMA (at  $\delta = 3.6$  ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of  $-\text{OCH}_2-$  protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA*n*BuMA) block.


The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA*n*BuMA-*b*-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature ( $T_g$ ) was determined as a midpoint of step change in heat flow curve for the second heating scan.


### $^1\text{H}$ NMR of MMA*n*BuMA*r*an [first block]:

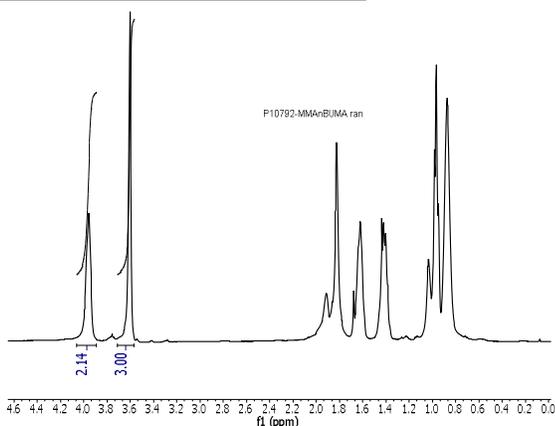


### $^1\text{H}$ NMR of MMA*n*BuMA*r*an-*b*-HEMA diblock copolymer:

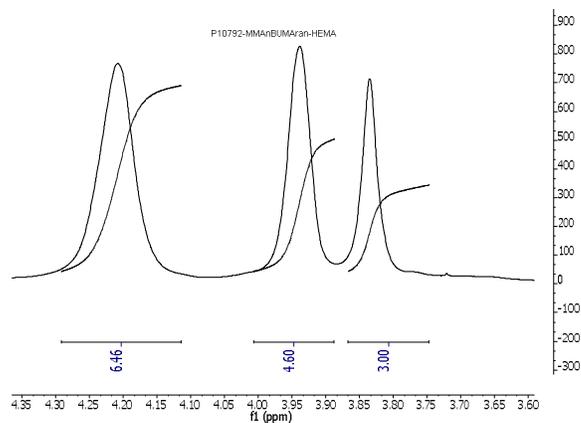

### SEC of MMA*n*BuMA*r*an [first block]:

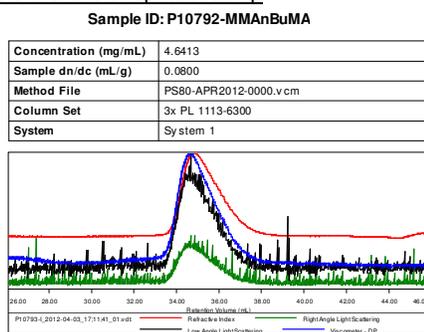


Sample	Mn (Da)	Mw (Da)	Mp (Da)	Mw/Mn	IV (dL/g)
P10793-1_2012-04-03_17:11:41_01.vdt	27,769	31,858	27,307	1.147	0.1871

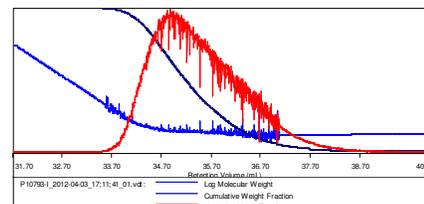

### SEC of MMA*n*BuMA*r*an and MMA*n*BuMA*r*an-*b*-HEMATMS:

#### P10792-MMA*n*BuMA*r*an-*b*-HEMA

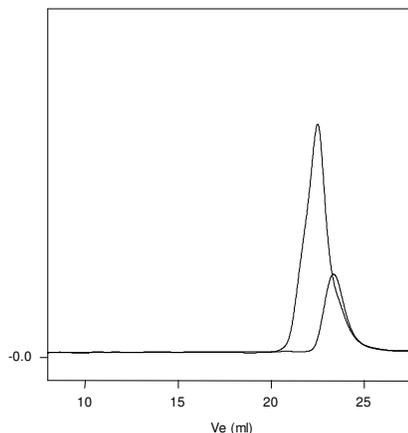

Size exclusion chromatography of  
1. MMA*n*BuMA*r*an block Mn 28,000 Mw 32,000 Mw/Mn 1.14  
2. MMA*n*BuMA*r*an-*b*-HEMATMS: 28,000-54,400 MW/Mn : 1.25  
After deprotection Mn 27,500-*b*-35,000 Mw/Mn 1.25