


Sample Name:
Ferrocenyl Dimethyl Silane Terminated
Polystyrene

Sample #: P9967B- SFerro

Structure:

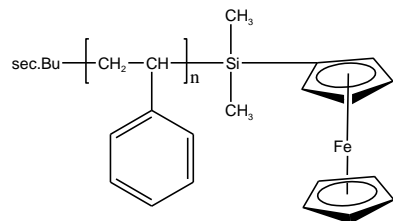

Composition:

$M_n \times 10^3$	PDI
65.0	1.25
T_g (°C)	103

Synthesis Procedure:

Ferrocenyl dimethyl silane terminated polystyrene was prepared by living anionic polymerization. The living polymer was terminated by ferrocenyl chlorodimethyl silane.

Characterization:

The molecular weight and polydispersity index of this polymer were determined by size exclusion chromatography (SEC) using a Varian liquid chromatograph equipped with a UV and refractive index detector. Polymer functionality was determined by titration with NaOH using phenolphthalein as the indicator.


Thermal analysis:

Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T_g) has been considered.

Solubility:


Polymer is soluble in toluene, THF, $CHCl_3$ and can be precipitated in hexane and methanol.

HNMR of the polymer:

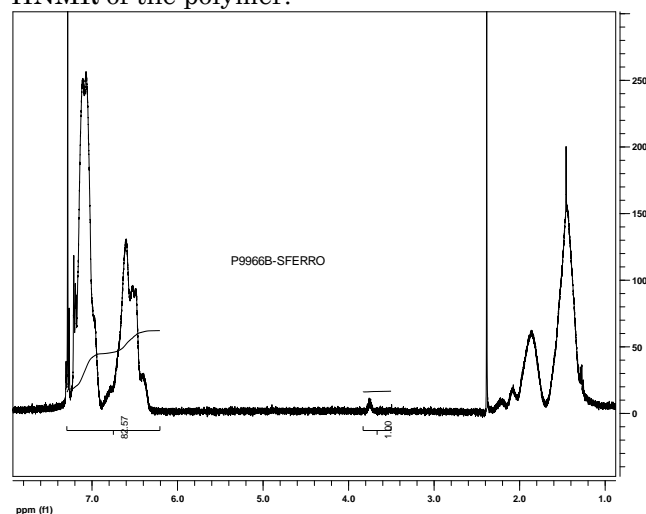

SEC for the sample:

P9967B-Sferro

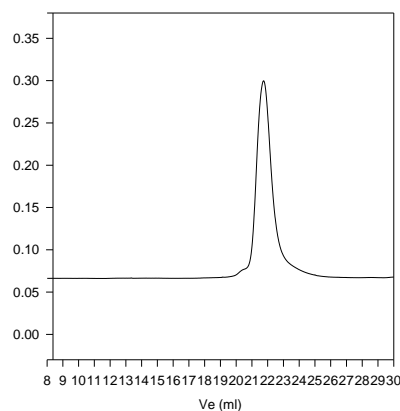

Size Exclusion chromatography of polystyrene terminated with ferrocene

— Polystyrene, $M_n=65,000$, $M_w=81,000$ PI=1.25

DSC thermogram for the sample:

