


Sample Name: Poly(methyl methacrylate-*co* (random)-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample # P40192-MMA-nBuMA-b-HEMA

Structure:

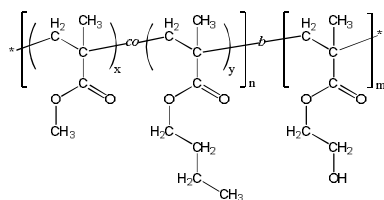

Composition:

$M_n \times 10^{-3}$ (g/mol)	25.0-20.5
M_w/M_n	1.23

Molar ratio MMA : nBuMA	50:50 (mol%)
Molar ratio MMA : HEMA	1 : 1.5
Molar ratio MMA-nBuMA : HEMA	57:43 (mol%)
Weight ratio MMA : nBuMA : HEMA	23:32:45 (wt %)

T_g (MMA-nBuMA block)	76 °C
T_g (HEMA block)	119 °C

Synthesis Procedure:

Poly (methyl methacrylate-*co*-n-butyl methacrylate)-*b*-poly(2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyl-protected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.


Solubility: The polymer is soluble in THF, DMF.

Characterization:

The polymer composition (molar ratio) was calculated by ^1H NMR. The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC) using DMF (0.023 M LiBr in DMF) as an eluent. Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.


^1H NMR of HEMA-TMS monomer (500 MHz, CDCl_3):

HEMA-TMS monomer (lot # P18658A)

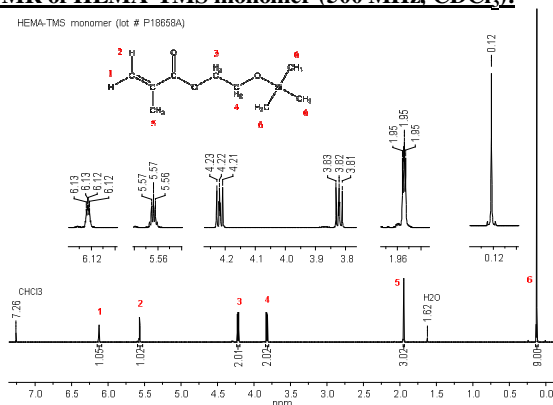


^1H NMR of MMA-nBuMA [first block] in CDCl_3 :

^1H NMR (500 MHz, CDCl_3): 40192-1_MMA-nBuMA

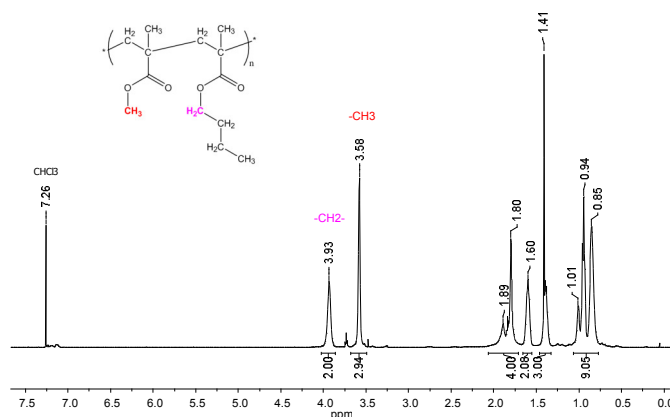


^1H NMR of MMA-nBuMA-b-HEMATMS [protected] in CDCl_3 :

^1H NMR (500 MHz, CDCl_3): 40192-2_MMA-nBuMA-b-HEMATMS

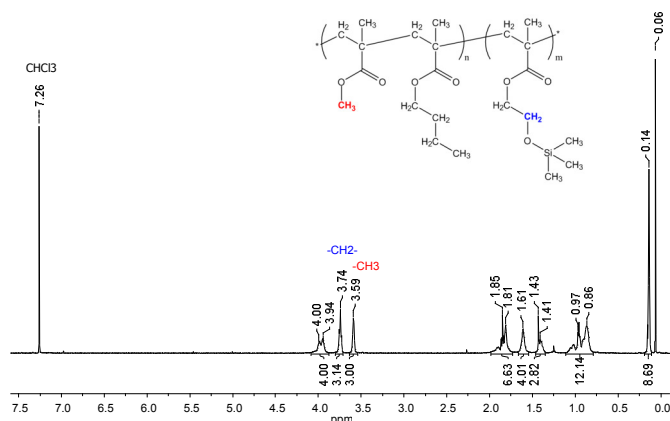

^1H NMR of [MMA-nBuMA]-b-HEMA [final] in DMF-d_7 :


^1H NMR (500 MHz, DMF-d_7): 40192-3_MMA-nBuMA-b-HEMA

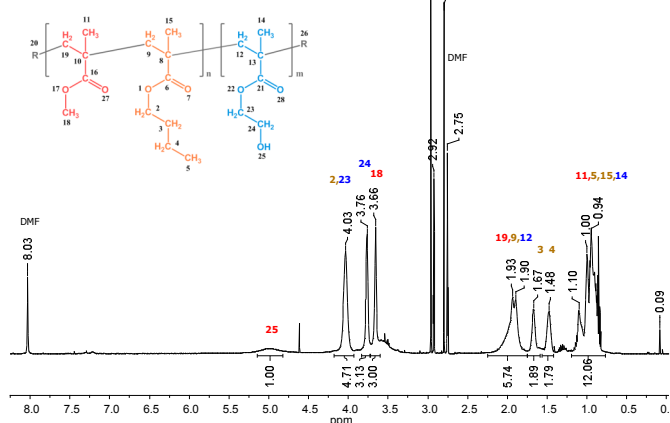

SEC elugram of MMA-nBuMA [first block]:

P40192-MMAAnBuMAran

Conc (mg/mL)	4.1093
dn/dc (mL/g)	0.0650
Method	PS80k-October2016-0000.vcm
Solvent	DMF w 0.023M LiBr
Column	PSS

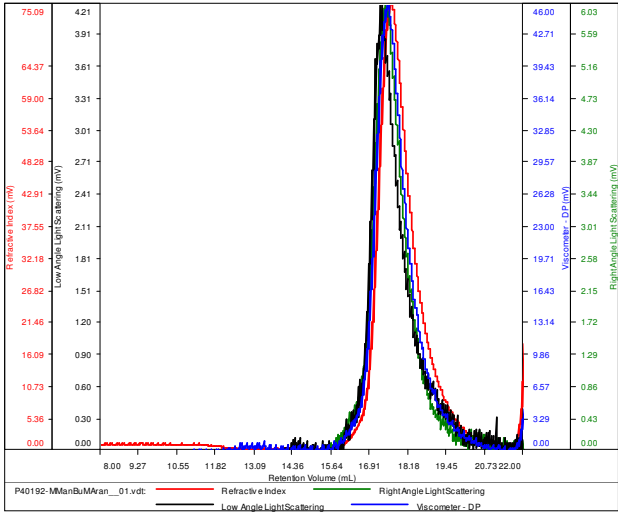


Sample	Mn	Mw	Mp	Mw/Mn	IV
P40192-MMAAnBuMAran__01.vdt	25,265	27,838	29,598	1.102	0.1696

SEC of MMAAnBuMA-b-HEMATMS [protected diblock]:

P40192-MMAAnBuMAran-HEMATMS

Conc (mg/mL)	26.2173
dn/dc (mL/g)	0.0650
Method	PS80k-December2016-0004.vcm
Solvent	DMF w 0.023M LiBr
Column	PSS

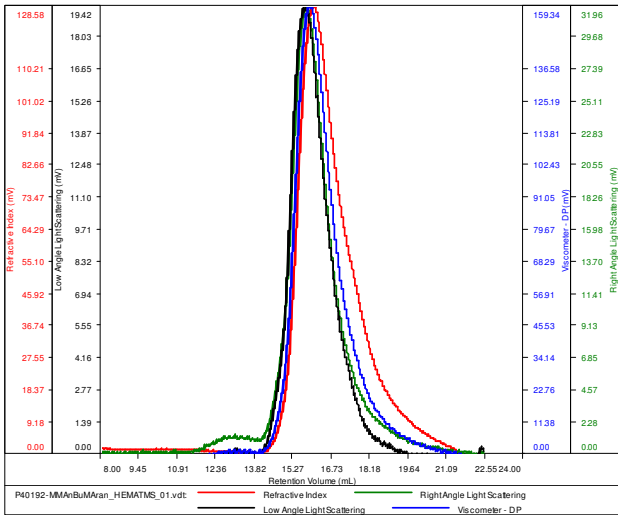

Sample	Mn	Mw	Mp	Mw/Mn	IV
P40192-MMAAnBuMAran_HEMATMS_01:	57,411	70,789	78,780	1.233	0.1289

DSC thermogram of MMAAnBuMA-b-HEMA diblock copolymer (2nd heating scan, 10°C/min):

