


Sample Name: Poly(ethylene oxide)-*b*-poly[(D,L-lactide)-*co*-glycolide]ran

Sample #: P40632-EO-*b*-LAGAran (DL form LA)




#### Composition:

$M_n \times 10^3$ (g/mol) [PEO- <i>b</i> -PLA- <i>co</i> -GA]	$M_w/M_n$
8.5- <i>b</i> -4.5- <i>co</i> -1.0	1.05

Glass transition temperature, $T_g$ :	-36 °C
Cold crystallization temperature, $T_{c,cr}$ :	-7 °C
Melting point, $T_m$ :	56 °C

#### Synthesis procedure:

The synthesis of poly(ethylene oxide)-*b*-poly[(D,L-lactide)-*co*-glycolide]ran is shown as follows:

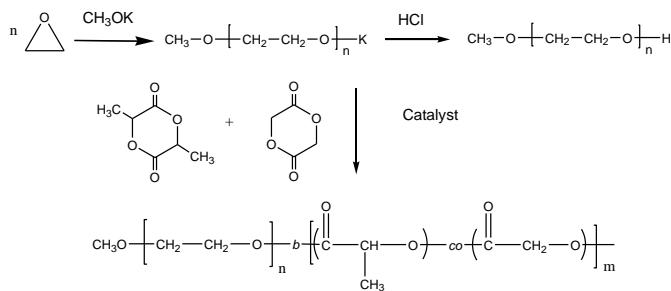

#### Characterization:

The molecular weight of the first block PEO was determined by  $^1\text{H}$  NMR and size exclusion chromatography (SEC). The final block copolymer composition was calculated from  $^1\text{H}$ -NMR spectroscopy by comparing the peak area of the methoxy-protons of poly(ethylene oxide) at around 3.6 ppm and the poly(lactide) protons at around 5.1 and 1.55 ppm and the poly(glycolide) protons at around 4.7 ppm. The polydispersity index ( $M_w/M_n$ ) of the block copolymer was obtained by SEC.


#### Thermal analysis:

Thermal analysis was performed on TA Instruments Q100 differential scanning calorimeter (DSC) under a nitrogen atmosphere. The glass transition temperature ( $T_g$ ) of the polymer was measured at a scan rate of 10°C/min shortly after creating thermal history of the sample.

#### Solubility:

The polymer is soluble in chloroform, THF, DMF, toluene; and it precipitates from ethanol, ether, and hexanes.


#### $^1\text{H-NMR}$ (500 Mhz, $\text{CDCl}_3$ ) spectrum of product:

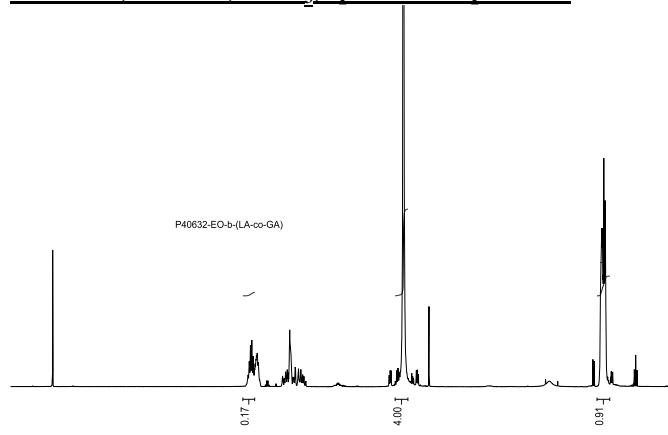

#### SEC elugram of the PEO (first block):

P40618-EGOCH3

Conc	82.9065
dn/dc	0.0440
Solvent	DMF w 0.023M LiBr
Flow Rate	0.7000
Method	P580k-May2017-0000.vcm

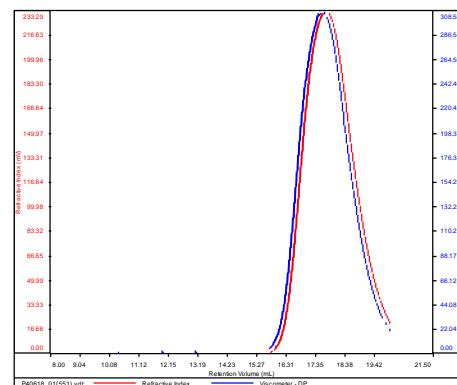


Sample	Mn	Mw	Mp	Mw/Mn	IV
P40618_01(551).vdt	8.537	8.863	7.895	1.038	0.0860

#### SEC elugram of the PEO-PLAGAran block copolymer:

P40632-EO-*b*-LAGA


Conc	46.0573
dn/dc	0.0340
Solvent	DMF w 0.023M LiBr
Flow Rate	0.7000
Method	P580k-May2017-0000.vcm

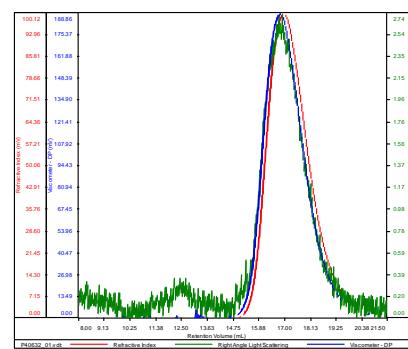

Sample	Mn	Mw	Mp	Mw/Mn	IV
P40632_01.vdt	14.655	15.283	14.754	1.043	0.0949

### **DSC thermograms of the polymer (10°C/min):**

2<sup>nd</sup> cooling scan [top curve] and 3<sup>rd</sup> heating scan [bottom curve]:

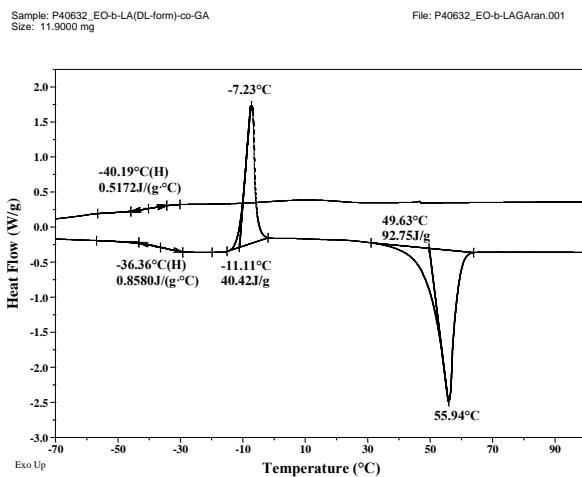

3<sup>rd</sup> heating scan (10 °C):

