

# Product Profile

## Identification

**Product Name:** Poly(styrene-b-4-vinyl-pyridine)

**Product Lot Number:** P19971-R-S4VP

**CAS #:** 26222-40-2

**Product Chemical Architecture:**



**Composition:**

Composition (S-b-4VP)	266,000-b-3,000
4VP mole%	1.0
Mn (g/mole)	269,000
Mw (g/mole)	276,000
Mw/Mn	1.03
dn/dc (mL/g) in DMF at 35 °C	0.165

## Method of Synthesis

The polymer is synthesized by anionic polymerization process.

**Solubility in different solvents:**

Solvent	Depends on composition	Solvent	✓
THF	Depends on composition	DMF	✓
Alcohol	Depends on composition	CHCl <sub>3</sub>	✓
Toluene <sub>(hot)</sub>	X	Water	X


## Validation of Architecture

### A. Gel Permeation Chromatography (GPC), SEC Profile:

Molecular weights were determined by Malvern OmniSec Reveal & Resolve GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LALS 7°) and two columns (PSS, SDV, 8x300 mm). DMF with 0.023M LiBr was the eluent. The flow rate was 0.7 ml/min.

Polymer Source

Malvern Panalytical

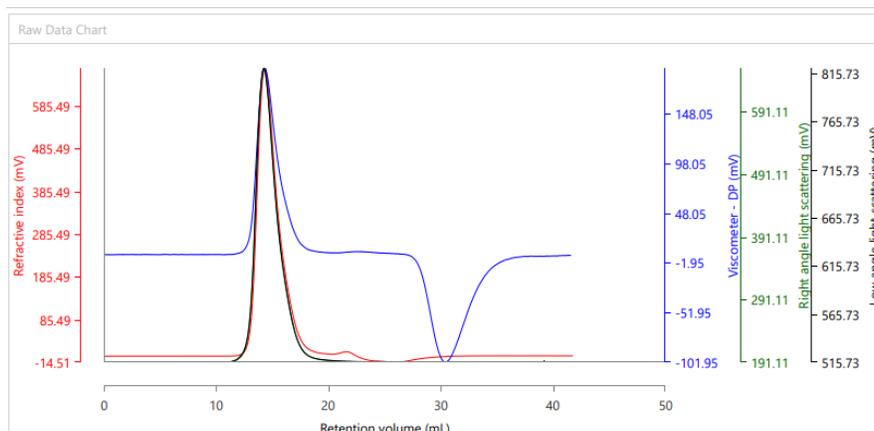

Injection Name	RV (mL)	Mn (g/mol)	Mw (g/mol)	Mp (g/mol)	Mz (g/mol)	Mw/Mn
P19971, Injection 1, Peak 1	14.34	268,956	275,724	265,776	290,758	1.025

B. NMR ( $^1\text{H}$ NMR) of S4VP in  $\text{CDCl}_3$ , 500 MHz

