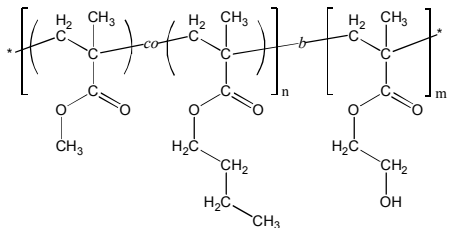


Sample Name:

Poly(methyl methacrylate-*co*_(random)-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample #: P11492p-MMA_nBuMA_ran-b-HEMA

Structure:**Composition:**

$M_n \times 10^3$ (g/mol)	22.0-25.0
M_w/M_n	1.15
Molar ratio MMA : nBuMA	75 : 25 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	32 : 15 : 53 (wt%)

Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.



Solubility: The polymer is soluble in THF, DMF.

Characterization:

The polymer composition was determined by ^1H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the $-\text{OCH}_2-$ protons of nBuMA (at $\delta = 3.9$ ppm) to the integration of methoxy group of MMA (at $\delta = 3.6$ ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of $-\text{OCH}_2-$ protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA_nBuMA) block.


The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA_nBuMA-b-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of $10^\circ\text{C}/\text{min}$. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.

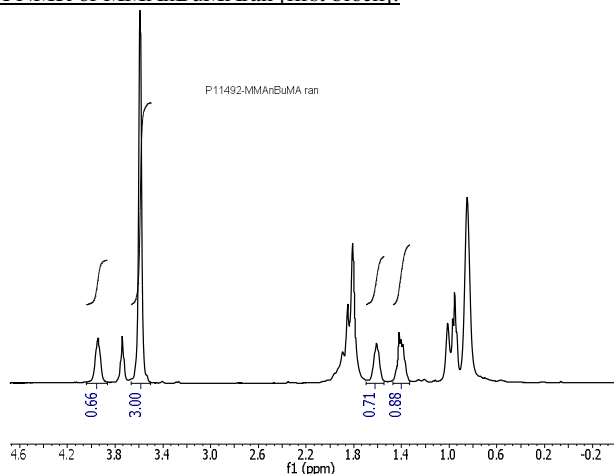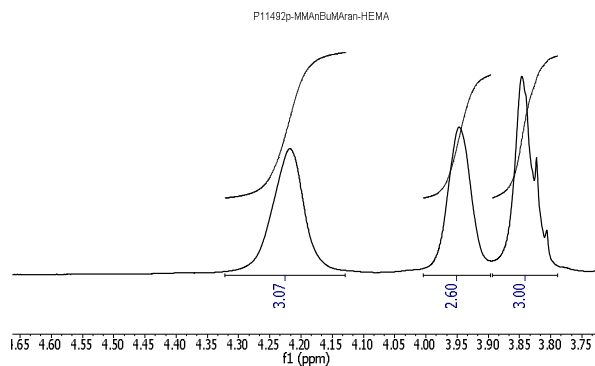
 ^1H NMR of MMA_nBuMA_ran [first block]: **^1H NMR of MMA_nBuMA_ran-b-HEMA diblock copolymer:****SEC of MMA_nBuMA_ran [first block]:**

Sample ID: P11492-1-MMA_nBuMA


Concentration (mg/mL)	7.0088
Sample dn/dc (mL/g)	0.0800
Method File	PS80K-May2013-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

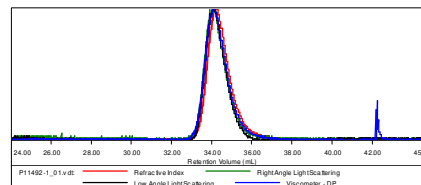

Sample	Mn	Mw	Mp	Mw/Mn	IV
P11492-1_01.vdt	21,803	23,024	22,944	1.056	0.2784

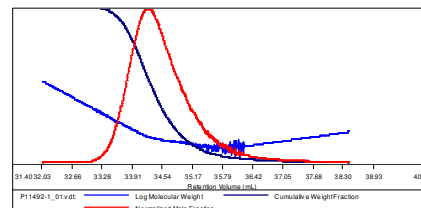**SEC of MMA_nBuMA_ran and MMA_nBuMA_ran-b-HEMATMS:**

P11492-MMA_nBuMA_ran-b-HEMA

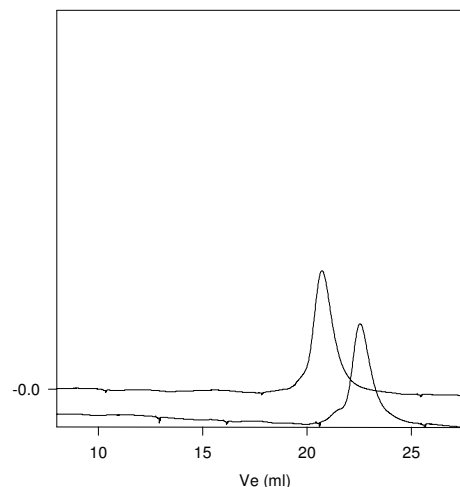

Size exclusion chromatography of

1. MMA_nBuMA_ran block Mn 22,000 Mw/Mn 1.05
2. MMA_nBuMA_ran-b-HEMATMS: 22,000-39,000 Mw/Mn : 1.15

After deprotection Mn 22,000-b-25,000 Mw/Mn 1.15