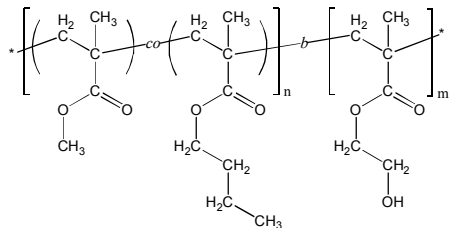


Sample Name:

Poly(methyl methacrylate-*co*_(random)-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample #: P11495p-MMA_nBuMA_ran-b-HEMA**Structure:****Composition:**

$M_n \times 10^3$ (g/mol)	22.0- <i>b</i> -28.0
M_w/M_n	1.15
Molar ratio MMA : nBuMA	70 : 30 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	27 : 17 : 56 (wt%)

Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

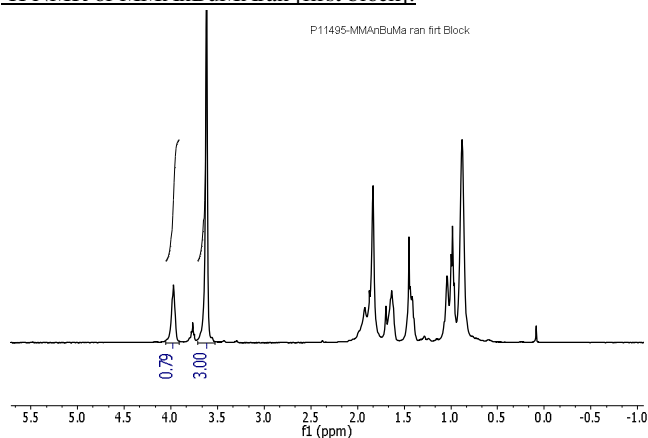
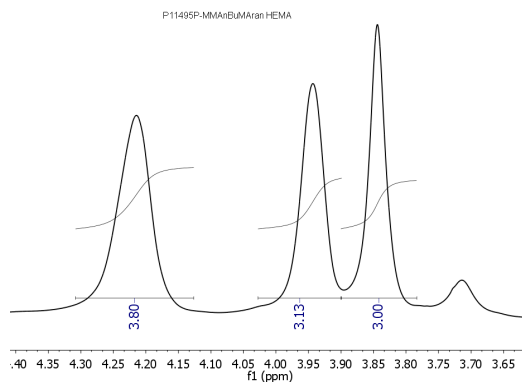
Solubility: The polymer is soluble in THF, DMF.

Characterization:

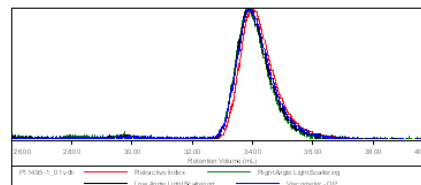
The polymer composition was determined by ^1H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the $-\text{OCH}_2-$ protons of nBuMA (at $\delta = 3.9$ ppm) to the integration of methoxy group of MMA (at $\delta = 3.6$ ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of $-\text{OCH}_2-$ protons of HEMA to the integration of methoxy group of MMA and using SEC data for the first (MMA_nBuMA) block.

The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA_nBuMA-*b*-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

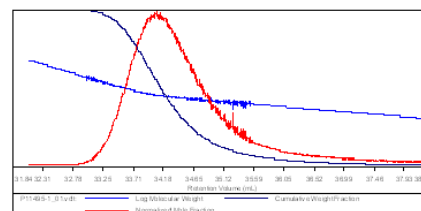
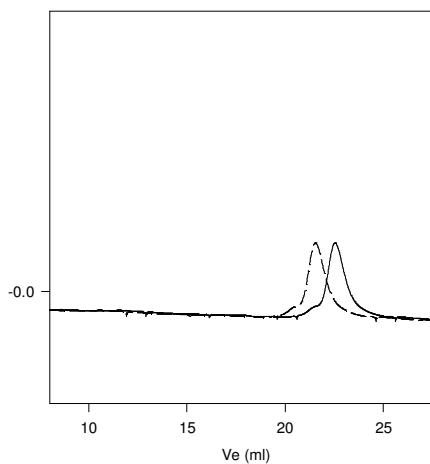
Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of $10^\circ\text{C}/\text{min}$. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.

 ^1H NMR of MMA_nBuMA_ran [first block]: **^1H NMR of MMA_nBuMA_ran-b-HEMA diblock copolymer:****SEC of MMA_nBuMA_ran [first block]:**Sample ID: P11495-1-MMA_nBuMA

Concentration (mg/L)	2.5089
Sample dilution (mL)	0.0500
Method File	PSS90-40x2013-0000.uem
Column Set	St P L 1113-6300
System	System 1



Sample	Mn	Mw	Mp	Mw/Mn	PDI
P11495-1_0.1x30	21,914	23,760	24,164	1.084	0.2913

**SEC of MMA_nBuMA_ran and MMA_nBuMA_ran-b-HEMATMS:**P11495-MMA_nBuMA_ran-b-HEMA

Size exclusion chromatography of
 1. MMA_nBuMA_ran block Mn 22,000 Mw/Mn 1.05
 2. MMA_nBuMA_ran-b-HEMATMS: 22,000-44,000 MW/Mn : 1.15
 After deprotection Mn 22,000-b-28,500 Mw/Mn 1.15