


Sample Name:

Poly urethane based on Adipic acid ,Butane diol and 4,4'-Methylenebis(phenyl isocyanate) MDI-based polyurethanes

Sample #: P14858-PU

Structure:



Composition:

M _w x 10 ³	M _w /M _n (PDI)	Composition Adipic acid: Butanediol:MDI	T _g (°C)
12.5	4.5	1:1:1	-15.1

Mn of Oligomers around 1,000

Synthesis Procedure:

Polyurethane is prepared in two-step procedure A: oligomerization of Adipic acid with Butane diol and then B reaction with MDI.

Characterization:

An aliquot of the copolymer was analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The chemical composition was verified by ¹H-NMR spectroscopy, which is run in deuterated chloroform at 500MHz. The glass-transition temperature was measured by DSC.

Solubility:

Chloroform (y)	THF (Y)	DMF (Y)	DMSO (Y)
(y)	(Y)	(Y)	(Y)

Figure: ¹H NMR spectrum


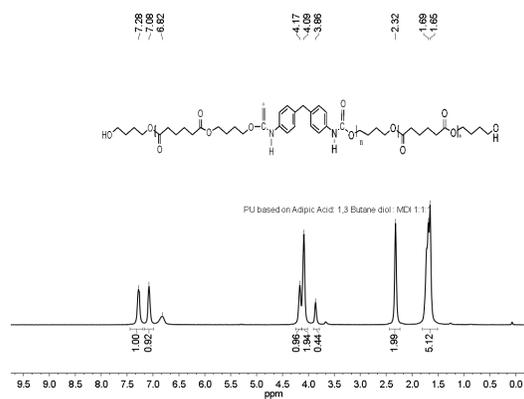


Figure: SEC profile of the polyurethane

Sample ID:P14858-PU

Concentration (mg/mL)	2.0714
Sample conc'd (mL/g)	0.1300
Method File	PS80K-April 29-2015-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

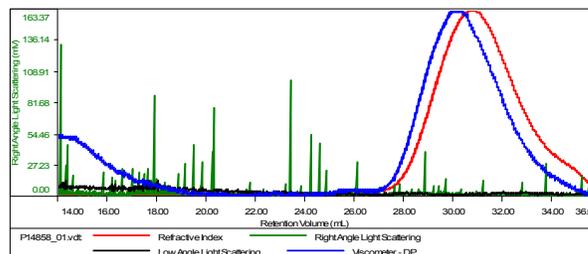

Sample	MN Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersi	Intrinsic Viscosity (dL/g)
P14858_01.vcl	2,768	12,555	2,442	4.535	0.6230

DSC Thermogram:

