


Sample Name: Poly(2-vinyl pyridine)

Sample #: P18016-2VP

Structure:

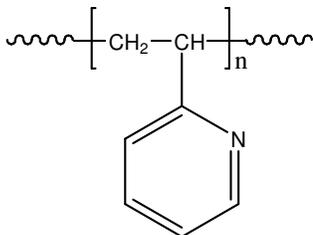


Composition:

$M_n \times 10^3$	PDI
717	1.4

Synthesis Procedure:

Poly(2-vinyl pyridine) is obtained by living anionic polymerization of 2-vinyl pyridine using an adduct of Sec. butyllithium and diphenyl ethylene-LiCl. Polymerization is carried out in THF at -78°C . Polymerization reaction is terminated using degassed methanol. The reaction scheme is illustrated as follows:

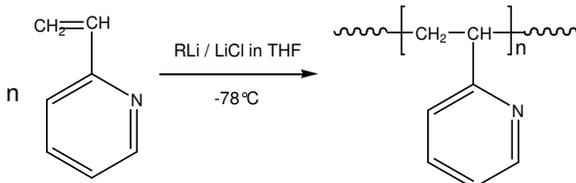

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.

Thermal analysis was performed on TA Instruments Q100 differential scanning calorimeter (DSC) under a nitrogen atmosphere. The glass transition temperature (T_g) of the polymer was measured at a scan rate of $10^\circ\text{C}/\text{min}$ shortly after creating thermal history of the sample.


Solubility:

Poly 2 vinylpyridine is soluble in DMF, THF, toluene, methanol, ethanol and CHCl_3 . It precipitates from water and hexanes, ether.


SEC elugram of the polymer:

Sample ID: P18016-2VP

Concentration (mg/mL)	0.8459
Sample dn/dc (mL/g)	0.1670
Method File	PS80K-May-2013-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

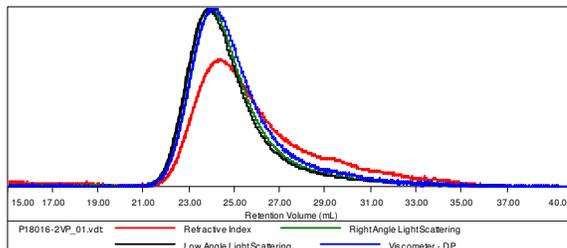

Sample	M_n	M_w	M_p	M_w/M_n	IV
P18016-2VP_01.vdt	717,450	991,957	1.224×10^6	1.383	3.0421

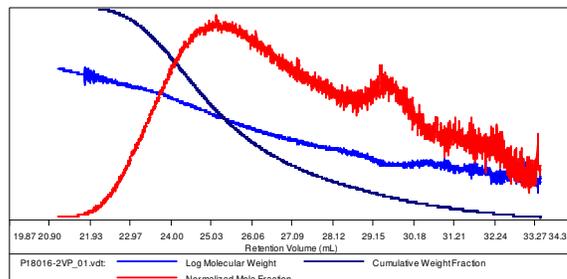

Relationship between T_g and M_n of P2VP:

