



Sample Name: Complete Deuterated Multiarm Polystyrene ;
Sample # P18515A-6dPS
6- arms Deuterated Poly styrene

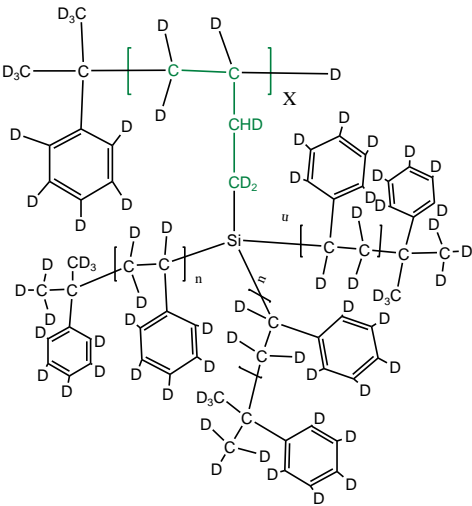


Linker : Lot# P18483A
SEC of the Polymer: (eah branch of Polystyrene)
Sample ID: P18515-DpS Branch

Concentration (mg/mL)	3.8844
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-Feb20-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

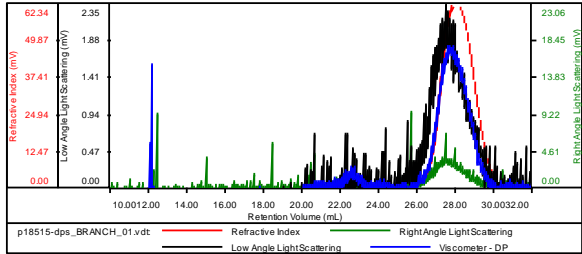


Sample	Mn	Mw	Mp	Mw/Mn	IV
p18515-dps_BRANCH_01.vdt	2,587	3,258	2,868	1.259	0.0388

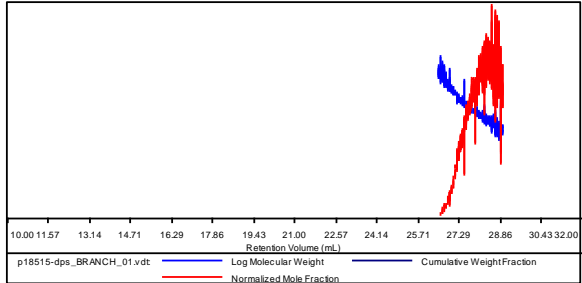


Sample ID: P18515a-dPS star

Concentration (mg/mL)	0.4579
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-Feb20-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

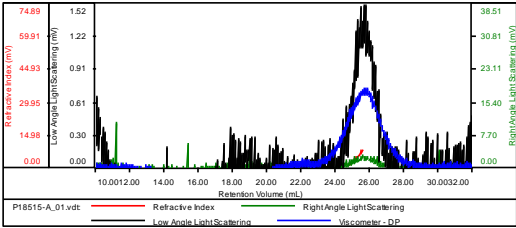

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18515-A_01.vdt	14,211	16,682	16,479	1.174	0.3870

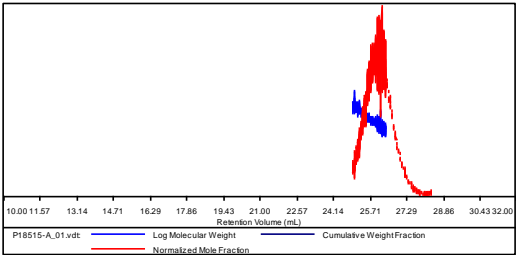

Mn x 10 ³ (total) 14.5 Mn of each arm: (2.5)	PDI 1.18
--	-------------

Synthesis Procedure:

