


Sample Name:

Poly(methyl methacrylate-*co*_(random)-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample #: P18664-MMA_nBuMA_ran-b-HEMA

Structure:

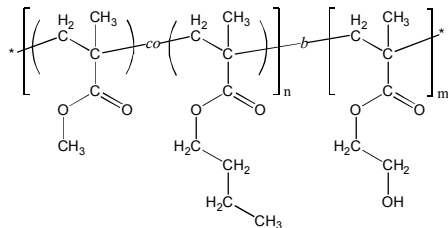

Composition:

$M_n \times 10^{-3}$ (g/mol)	18.0- <i>b</i> -21.0
M_w/M_n	1.14
Molar ratio MMA : nBuMA	60 : 40 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	24 : 22 : 54 (wt%)

Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

Solubility: The polymer is soluble in THF, DMF.


Characterization:

The polymer composition was determined by ^1H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the $-\text{OCH}_2-$ protons of nBuMA (at $\delta = 3.9$ ppm) to the integration of methoxy group of MMA (at $\delta = 3.6$ ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of $-\text{OCH}_2-$ protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA_nBuMA) block.


The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA_nBuMA-b-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of $10^\circ\text{C}/\text{min}$. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.


^1H NMR of MMA_nBuMA_ran [first block] in CDCl_3 :

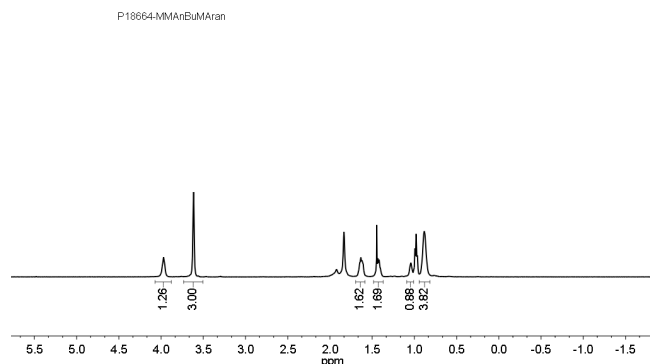


^1H NMR of HEMATMS monomer (500 MHz, CDCl_3):

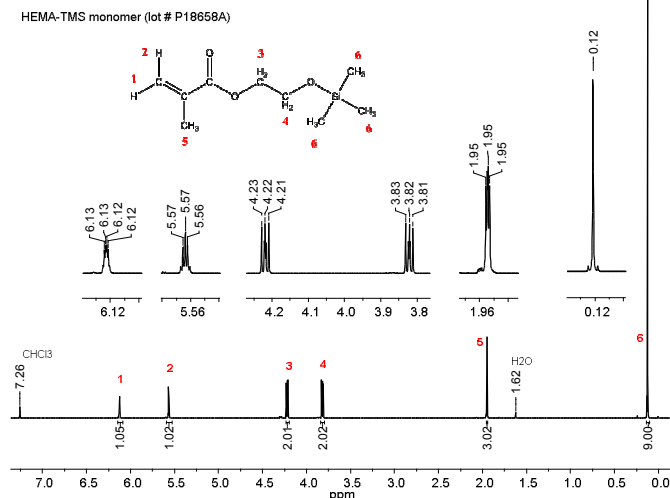

^1H NMR of MMA_nBuMA_ran-b-HEMATMS in CDCl_3 :

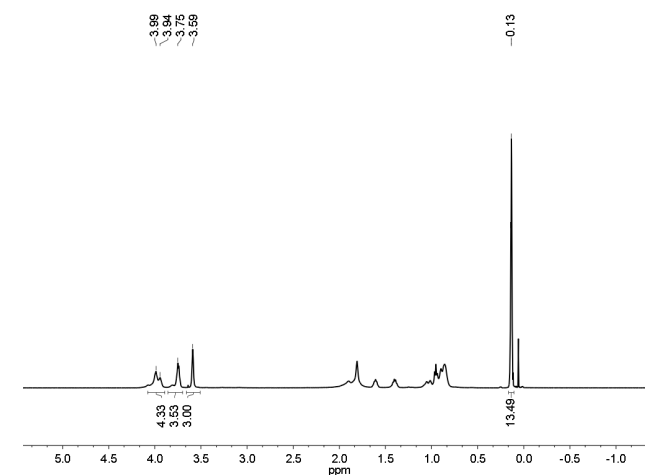


^1H NMR of MMA_nBuMA_ran-b-HEMA in DMF-d_7 :

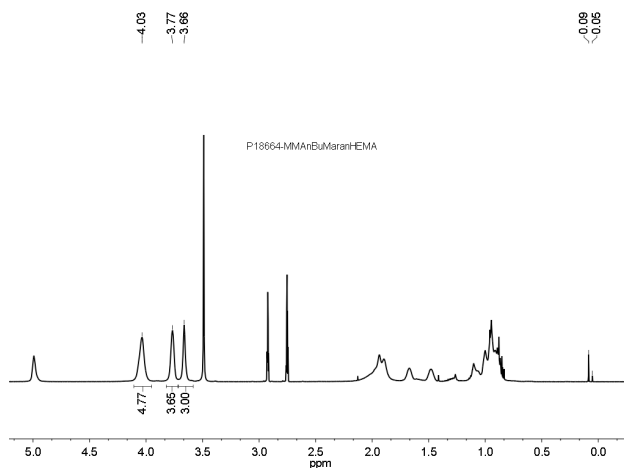


SEC of MManBuMAran [first block]:

Sample ID: P18664-1-MMABuMA

Concentration (mg/mL)	11.2938
Sample dn/dc (mL/g)	0.0840
Method File	PS 80K-Apr15-2014-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

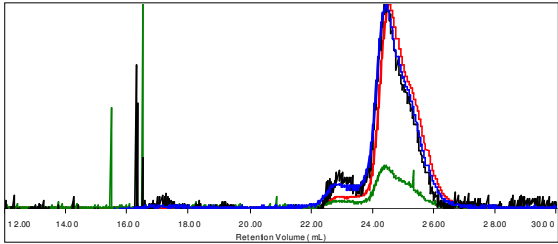


Sample	Mn	Mw	Mp	Mw/Mn	IV
P18664-1-redo_01.vdt	18,053	21,674	18,166	1.201	0.0549

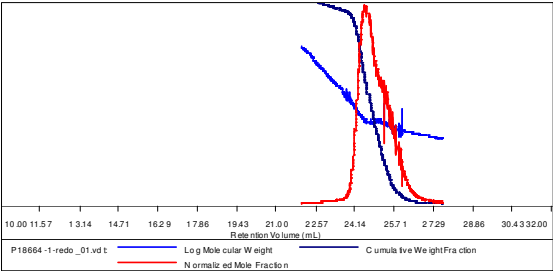

SEC of MManBuMAran-b-HEMATMS:

Sample ID: P18664-2

Concentration (mg/mL)	4.5374
Sample dn/dc (mL/g)	0.0694
Method File	PS80K-June29-2014-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

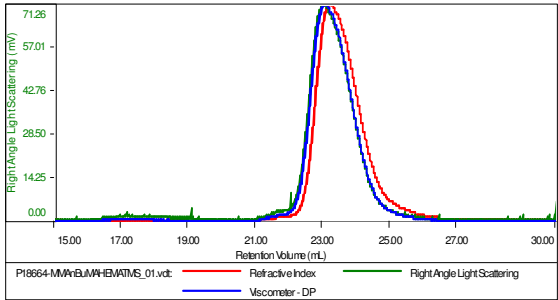

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18664-MManBuMAran-b-HEMATMS_01.vdt	50,331	57,436	56,057	1.141	0.9126

