


Sample Name:
Hydroxy Terminated Poly(2-Vinyl Pyridine)
Sample #: P19136-2VPOH

Structure:

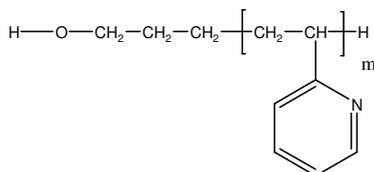


Composition:

$M_n \times 10^3$	PDI
17.5	1.14
Functionality %	>99%
T_g for the functional polymer	78°C

Synthesis Procedure:

Hydroxy terminated poly(2-vinyl pyridine) was prepared by living anionic polymerization of 2-vinyl pyridine in THF using OH protected initiator. The scheme of the reaction is illustrated below:

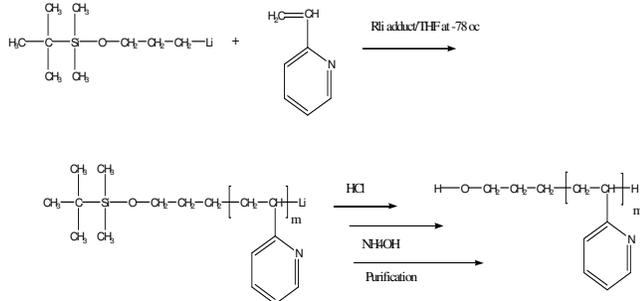

Characterization:

The molecular weight and polydispersity index of this polymer were determined by size exclusion chromatography (SEC) using a Varian liquid chromatograph equipped with a UV and refractive index detector.

Thermal analysis:

Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T_g) has been considered.


Solubility:

Polymer is soluble in CHCl_3 and THF.

SEC of Sample:

Sample ID: P19136-2VPOH

Concentration (mg/mL)	11.2805
Sample dn/dc (mL/g)	0.1670
Method File	PS90K-March6-2015-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

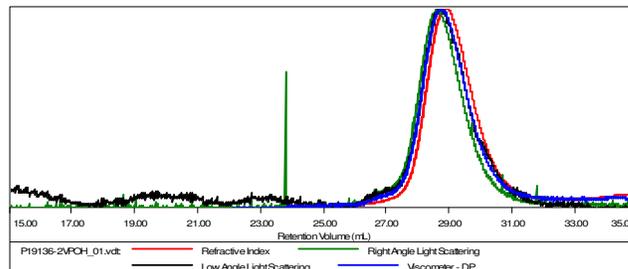

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P19136-2VPOH_01.vdt	17,585	20,025	19,783	1.139	0.0805

H NMR:

