


Sample Name: **Carboxy-terminated Polybutadiene (1,2-rich microstructure)**
Sample #: **P19264-BdCOOH**

Structure:

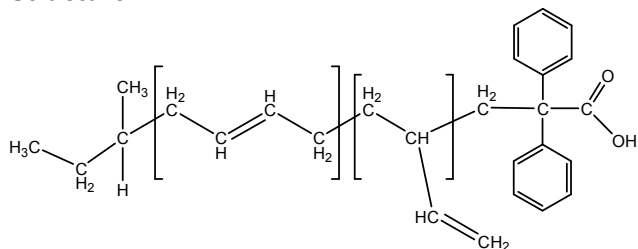

Composition:

Mn x 10 ³	PDI
2.0	1.15
1.8 (HNMR)	
COOH functionality:	> 98 %
PBd 1,2-addition:	32 %

Synthesis Procedure:

1,2-addition carboxy-terminated polybutadiene was prepared by anionic living polymerization of butadiene in non-polar media, followed by termination of the polymerization with dried CO₂ in presence of THF to avoid any linking reaction with CO₂.

Characterization:


By GPC and HNMR. .

Functionality: The degree of polymer functionality was determined by acid-base titration.

Microstructure: The ratio between 1,4- and 1,2-addition was calculated by ¹H NMR spectroscopy.

Solubility:


COOH terminated polybutadiene is soluble in DMF, THF, toluene, hexane, cyclohexane and CHCl₃. It precipitates from methanol, ethanol and water.

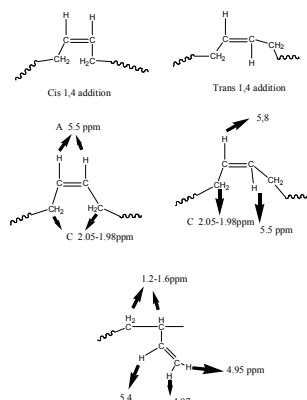

SEC of Sample:

Sample ID: P19264-BdCOOH

Concentration (mg/mL)	6.6739
Sample dn/dc (mL/g)	0.1670
Method File	PS80K-April29-2015-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

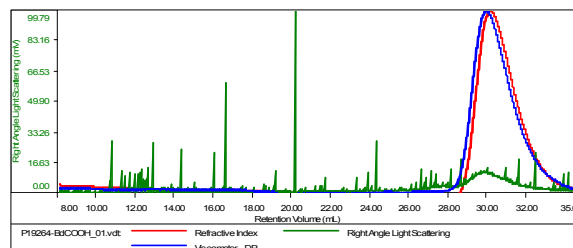

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P19264-BdCOOH_01.vdt	1,974	2,020	1,985	1.023	0.4351

¹H NMR spectrum:

