


Sample Name:

Poly urethane based on Adipic acid, Butane diol and 4,4'-Methylenebis(phenyl isocyanate) MDI-based polyurethanes

Sample #: P19344-PU

Structure:



Composition:

Mw x 10 <sup>3</sup>	Mw/Mn (PDI)	Composition Adipic acid: Butanediol:MDI	Tg (°C)
10.0	1.9	1:1:1	-15.1

**Mn of Oligomers : Trimer of Adipic acid and butandiol: 3000**

**Synthesis Procedure:**

Polyurethane is prepared in two-step procedure A: oligomerization of Adipic acid with Butane diol and then B reaction with MDI.

**Characterization:**

An aliquot of the copolymer was analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The chemical composition was verified by <sup>1</sup>H-NMR spectroscopy, which is run in deuterated chloroform at 500MHz. The glass-transition temperature was measured by DSC.

**Solubility:**

Chloroform (Y)	THF (y)	DMF (Y)	DMSO (Y)
----------------	---------	---------	----------

Figure: <sup>1</sup>H NMR spectrum


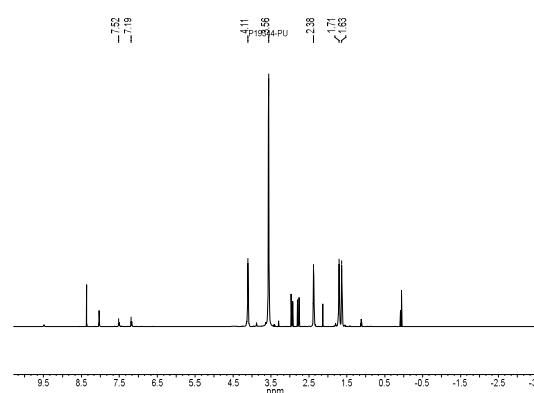


Figure: SEC profile of the polyurethane  
SAMPLE ID: P19344-PU

Conc (mg/mL)	6.0245
dn/dc (mL/g)	0.1100
Method	ps80k-May2015-0000.vcm
Solvent	DMF w 0.03MLibr
Column	PSS

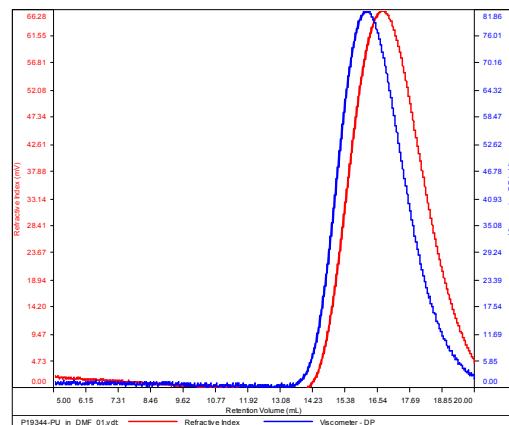

Sample	Mn	Mw	Mp	Mw/Mn	IV
P19344-PU_in_DMF_01.vdt	5,218	9,925	8,150	1.902	0.4074

DSC Thermogram:

