


## Sample Name:

Poly(methyl methacrylate-*co*<sub>(random)</sub>-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

## Sample #: P19345-MMAAnBuMAran-b-HEMA

### Structure:

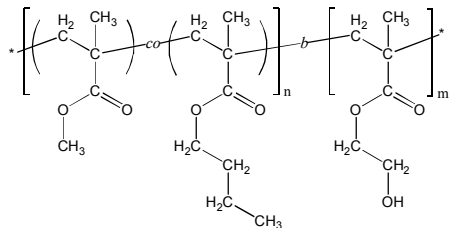

### Composition:

$M_n \times 10^3$ (g/mol)	33.0-36.5
$M_w/M_n$	1.4
Molar ratio MMA : nBuMA	55 : 45 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	22 : 26 : 52 (wt%)

### Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

**Solubility:** The polymer is soluble in THF, DMF.


### Characterization:

The polymer composition was determined by  $^1\text{H}$  NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the  $-\text{OCH}_2-$  protons of nBuMA (at  $\delta = 3.9$  ppm) to the integration of methoxy group of MMA (at  $\delta = 3.6$  ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of  $-\text{OCH}_2-$  protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMAAnBuMA) block.


The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMAAnBuMA-b-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of  $10^\circ\text{C}/\text{min}$ . The glass transition temperature ( $T_g$ ) was determined as a midpoint of step change in heat flow curve for the second heating scan.


## $^1\text{H}$ NMR of HEMATMS monomer in $\text{CDCl}_3$ :

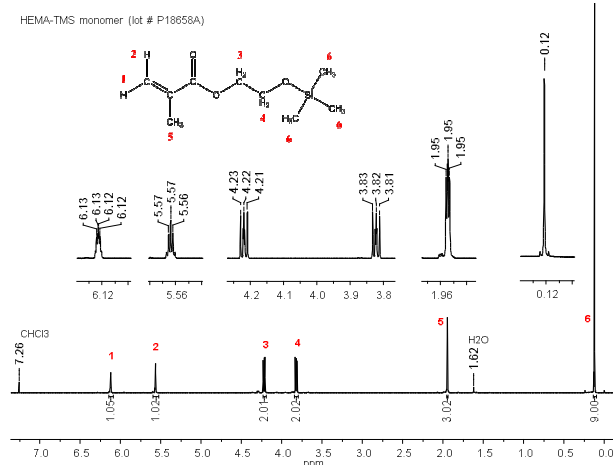

## $^1\text{H}$ NMR of MMAAnBuMAran [first block]:

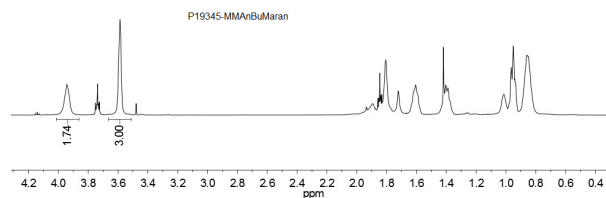


## $^1\text{H}$ NMR of MMAAnBuMAran-b-HEMATMS in $\text{CDCl}_3$ :

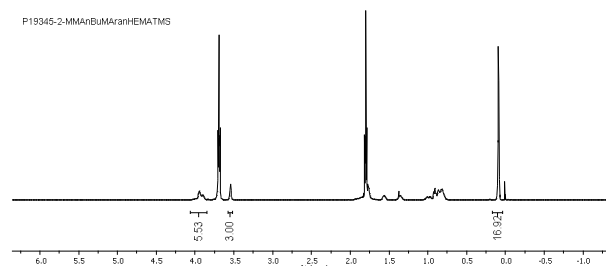

## SEC of MMAAnBuMAran [first block]:

SAMPLE ID: P19345-1

Conc (mg/mL)	6.7959
dn/dc (mL/g)	0.0650
Method	ps80k-May2015-0000.vcm
Solvent	DMF w 0.03M LiBr
Column	PSS

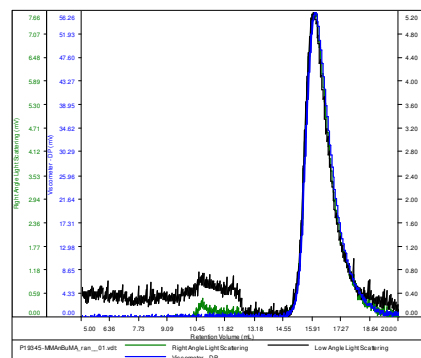


Sample	Mn	Mw	Mp	Mw/Mn	PDI
P19345-MMAAnBuMA_ran_01.vdt	32,930	36,646	38,729	1.113	0.1301

## SEC of MMAAnBuMAran and MMAAnBuMA-b-HEMATMS:

SAMPLE ID:  
P19345-2-MMAAnBuMAranHEMATMS

Conc (mg/mL)	30.2234
dn/dc (mL/g)	0.0680
Method	ps80k-July2015-0000.vcm
Solvent	DMF w 0.03M LiBr
Column	PSS

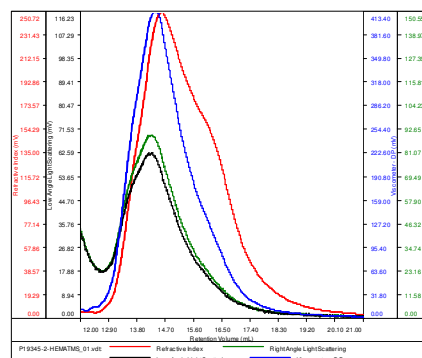

Sample	Mn	Mw	Mp	Mw/Mn	PDI
P19345-2-HEMATMS_01.vdt	89,816	127,292	135,340	1.417	0.3227