


Sample Name:

Poly(methyl methacrylate-co_(random)-n-butyl methacrylate)-block-poly(2-hydroxyethyl methacrylate)

Sample #: P19348-MMA_nBuMA_ran-b-HEMA

Structure:

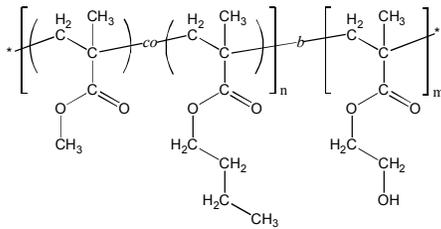

Composition:

$M_n \times 10^3$ (g/mol)	56.0- <i>b</i> -16.5
M_w/M_n	1.37
Molar ratio MMA : nBuMA	52 : 48 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	33 : 44 : 23 (wt%)

Synthesis Procedure:

Poly([methyl methacrylate-co-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

Solubility: The polymer is soluble in THF, DMF.


Characterization:

The polymer composition was determined by ¹H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the -OCH₂-protons of nBuMA (at δ = 3.9 ppm) to the integration of methoxy group of MMA (at δ = 3.6 ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of -OCH₂- protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA_nBuMA) block.


The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA_nBuMA-*b*-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.


¹H NMR of MMA_nBuMA_ran [first block] in CDCl₃:

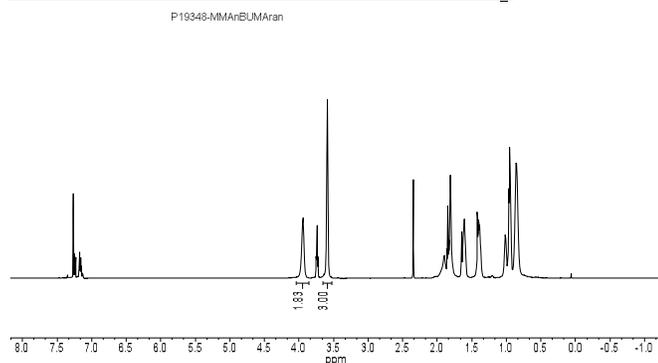

¹H NMR of HEMATMS monomer in CDCl₃:

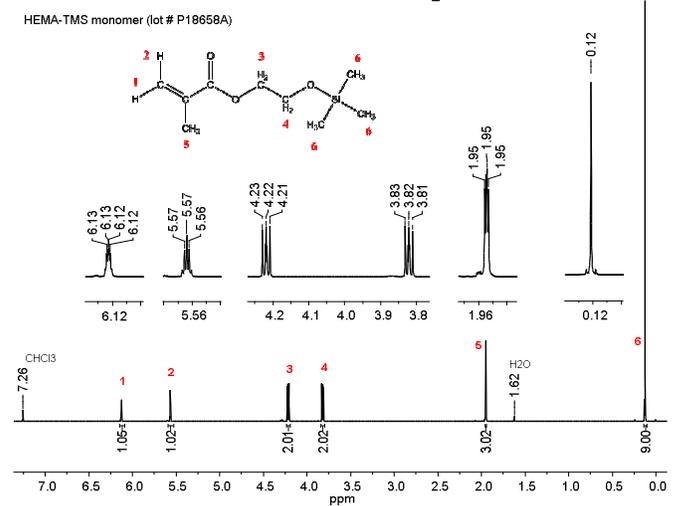

¹H NMR of MMA_nBuMA_ran-b-HEMATMS in CDCl₃:

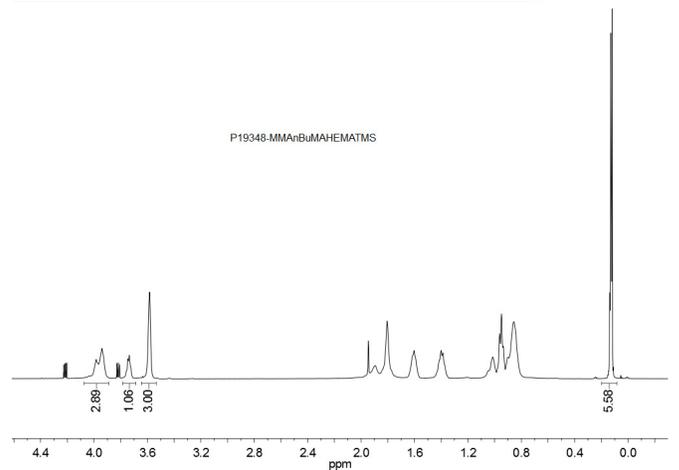


SEC of MMA_nBuMA_ran [first block]:

Sample

ID:P19348-MMA_nBuMA_ran

Concentration (mg/mL)	1.3864
Sample conc: (mL/g)	0.0840
Method File	PS80K-June30-2015-0000.vcm
Column Set	3x PL 1113.6300
Solvent	THF

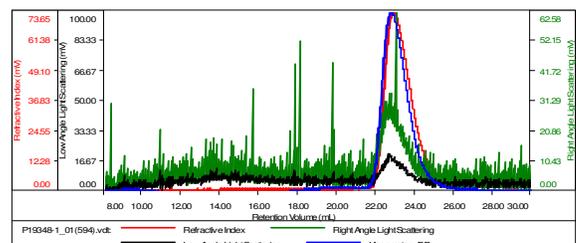


Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P19348-1_01(594).vcl	55,925	67,759	52,700	1.212	0.9485

SEC of MManBuMAran and MManBuMA-b-HEMATMS:

Sample ID: P19348-2

Concentration (mg/mL)	2.0738
Sample dryc: (mL/g)	0.0530
Method File	PS80K-June30-2015-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

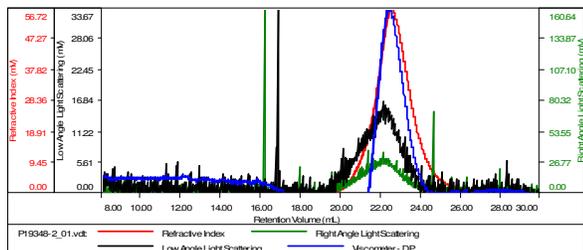

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersi	Intrinsic Viscosity (dL/g)
P19348-2_01.vct	90,420	124,214	95,393	1.374	0.3690