


Sample Name:

Poly(methyl methacrylate-*co*_(random)-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample #: P19430-MMA_nBuMA_ran-b-HEMA

Structure:

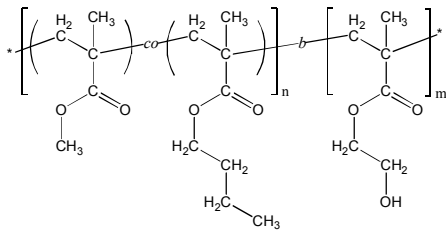

Composition:

$M_n \times 10^3$ (g/mol)	31.0- <i>b</i> -38.0
M_w/M_n	1.33
Molar ratio MMA : nBuMA	55 : 45 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	21 : 24 : 55 (wt%)
T_g (MMA _n BuMA)	80 °C
T_g (HEMA)	113 °C

Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

Solubility: The polymer is soluble in THF, DMF.


Characterization:

The polymer composition was determined by ¹H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the -OCH₂- protons of nBuMA (at δ = 3.9 ppm) to the integration of methoxy group of MMA (at δ = 3.6 ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of -OCH₂- protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA_nBuMA) block.

The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA_nBuMA-b-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.


¹H NMR of MMA_nBuMA_ran [first block]:

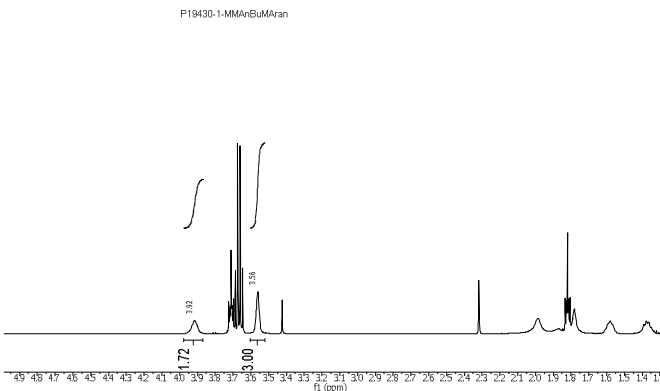

SEC of MManBuMAran-b-HEMATMS:

SAMPLE ID:
P19430-2-MManBuMAranHEMATMS

Conc (mg/mL)	24.7835
dn/dc (mL/g)	0.0680
Method	ps80kJuly292015-0000.vcm
Solvent	DMF w 0.03MLiBr
Column	PSS

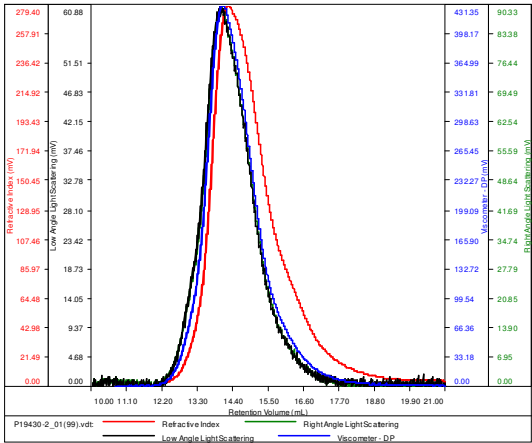

Sample	Mn	Mw	Mp	Mw/Mn	IV
P19430-2_01(99).vdt	87,434	116,681	128,549	1.334	0.3428

DSC of MManBuMAran-b-HEMA:

