


Sample Name: Poly(4-chloro styrene)

Sample #: P19639A-4CIS

Structure:




Composition:

$M_n \times 10^3$	PDI
89.0	1.38

Synthesis Procedure:

Poly(4-chloro styrene) is synthesized by free radical polymerization of 4-chloro styrene and the reaction scheme is shown below.

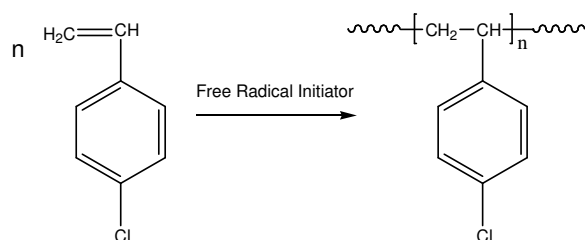

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC).


Solubility:

Poly(4-chloro styrene) is soluble in DMF, THF, toluene and $CHCl_3$. It precipitates from methanol, ethanol, water and hexanes.

SEC of Homopolymer:

Sample ID-P19639A-4CIS

Concentration (mg/mL)	0.2044
Sample dn/dc (mL/g)	0.1850
Method File	PS30K-June30-2015-0000.vom
Column Set	3x PL 1113-6300
Solvent	THF

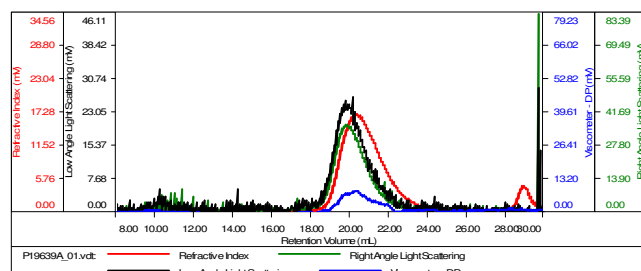

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P19639A_01.vcl	89,176	123,734	134,784	1.398	2.1637