


Sample Name:

Amino-terminated poly(N-isopropyl acrylamide)

Sample # P20148B-NIPAMNH2

Structure:

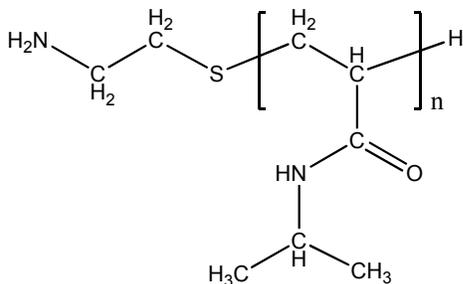


Composition:

$M_n \times 10^3$ (g/mol)	$M_w/M_n$
53.5	1.6

Synthesis Procedure:

Amino-terminated poly(N-isopropyl acrylamide) was prepared by free-radical polymerization of N-isopropyl acrylamide in presence of an amino-group containing chain-transfer agent. The product was purified by fractionation. The scheme of reaction is shown below:

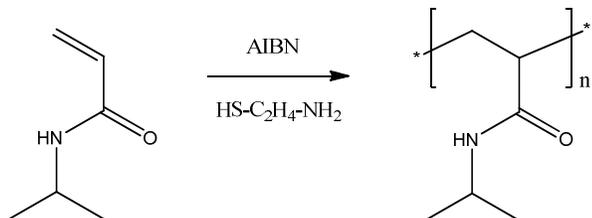

Characterization:

The molecular weight and functionality degree of the polymer were calculated by titration using HClO<sub>4</sub>/Crystal violet in CHCl<sub>3</sub>/acetic acid. The polydispersity index ( $M_w/M_n$ ) was determined by size exclusion chromatography (SEC) on a Varian liquid chromatograph equipped with a triple detector.


Solubility:

The polymer is soluble in water, THF, chloroform and dichloromethane; and is insoluble in hexane and ether.

SEC elugram of the polymer:

SAMPLE ID: P20148B-NIPAM-NH2

Conc (mg/mL)	10.3780
dn/dc (mL/g)	0.0770
Method	PS80K-17SEP2014-0000.vcm
Solvent	DMF w 0.03MLiBr
Column	PSS

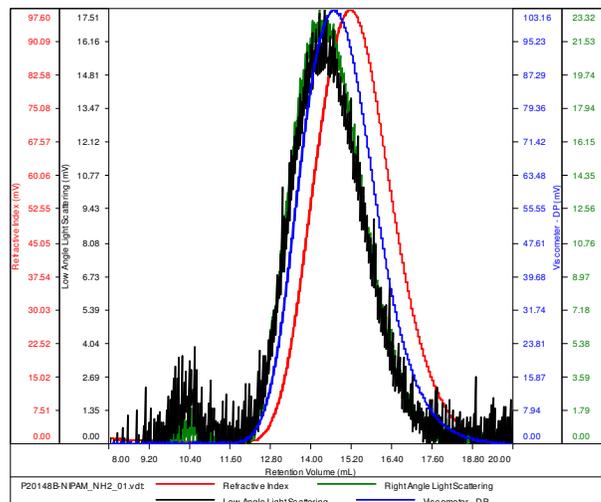

Sample	Mn	Mw	Mp	Mw/Mn	IV
P20148B-NIPAM_NH2_01.vdt	53,601	84,259	68,496	1.572	0.2946