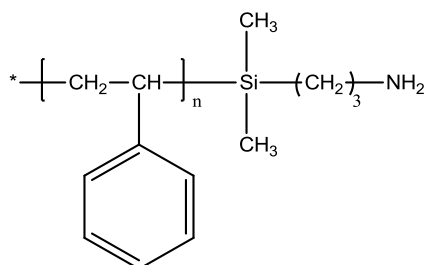
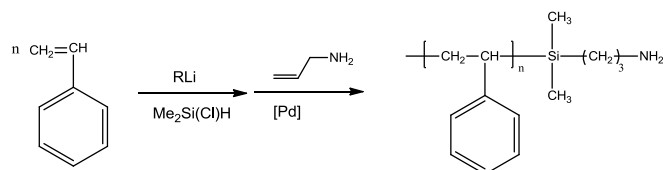


Sample Name: Amino-Terminated Polystyrene**Sample #:** P3956-SNH2**Structure:****Composition:**

$M_n \times 10^3$	M_w/M_n	-NH ₂ functionality
11.0	1.10	> 98 %


Synthesis Procedure:

α -Amino-terminated polystyrene was synthesized by anionic living polymerization. The reaction scheme is shown below:

**Characterization:**

The molecular weight and polydispersity index (M_w/M_n) of the polymer were determined by size exclusion chromatography (SEC) using a Varian liquid chromatograph equipped with a UV and refractive index detector. As amino-terminated polystyrene interacts with chromatography columns, amino-group was protected by reaction with 1-naphthyl isocyanate before SEC analysis. Removal of the protecting group was confirmed by UV spectroscopy, and the degree of functionality was confirmed by titration with $HClO_4$ using crystal violet as the indicator.

Solubility: The polymer is soluble in THF, $CHCl_3$, and toluene. It precipitates from methanol and hexane.

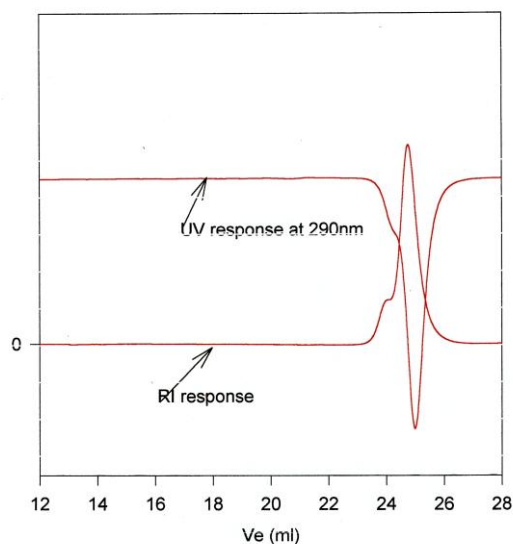SEC elugram of the end-group protected polymer:**P3956-SNH2**

Size exclusion chromatography of monoamino terminated terminated polystyrene. (NH₂ group end capped with 1-naphthyl isocyanate)
 $M_n=11000$, $M_w=12000$, $PI=1.10$, functionality=0.98.