


Sample Name: Amino Terminated Polybutadiene, 1, 2- rich microstructure

Sample #: P3975A-BdNH2

Structure:

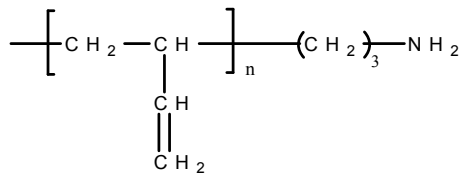


Composition:

| | |
|----------------------|-------|
| Mn x 10 ³ | PDI |
| 3.0 | 1.08 |
| Functionality | >80% |
| T _g | -31°C |

Synthesis Procedure:

Amino terminated polybutadiene (1,2 addition) was prepared by anionic living polymerization of butadiene in polar solvent such as THF with initiation by an amino protected organo-lithium compound such as 2, 2,5,5-tetramethyl-1-(3-lithiopropyl)-1-aza-2,5-disilacyclopentane or termination of polymerization reaction (initiated by Sec. BuLi initiator) by 2,2,5,5-tetramethyl-1-(3-chloropropyl)-1-aza-2,5-disilacyclopentane, followed by deprotection of NH₂ functional group. The scheme of the reaction is illustrated below:

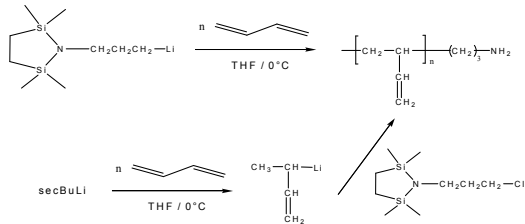


Characterization:

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co. **Functionality:** The functionality of polymer was determined by the titration with HClO₄ using crystal violet as the indicator **Thermal Analysis:** Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 15°C/min. The inflection glass transition temperature (T_g) of the sample has been considered.

P3975A-BdNH2 (1, 2 addition)

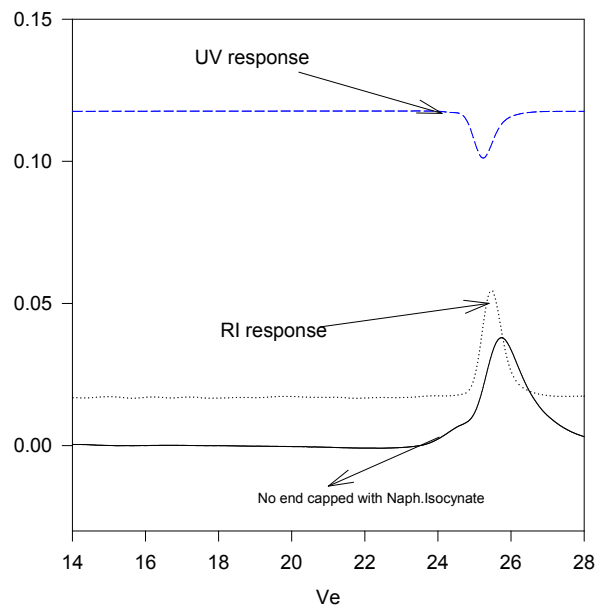

Size Exclusion Chromatography :

..... Mn: 3000 Mw: 3300 Mw/Mn 1.08 Functionality: > 98%
 - - - - UV response at 290nm after end capping NH₂ group with 1-Naphthyl isocyanate

