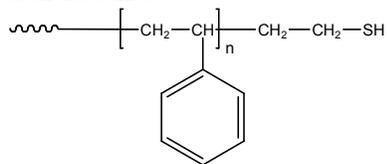



Sample Name:**Thiol Terminated Polystyrene****Sample #: P4422-SSH****Structure:****Composition:**

Mn x 10 ³	PDI
2.5	1.05
SH- Functionality	>60%
T _g (°C)	52

Synthesis Procedure:

SH end functionalized polystyrene can be synthesized quantitatively by 2 different approaches:

1. From hydroxy terminated polymer as illustrated below:

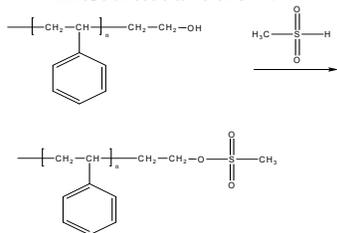

2. From direct termination of anionic living polymerization of styrene by ethylene sulfide or propylene sulfide. Polymerization of styrene by Sec.BuLi in THF at -78 °C and termination by purified ethylene sulfide or propylene sulfide.

Characterization:


The molecular weight and polydispersity index of the hydroxyl terminated polymer were determined before functionalization with thiol by size exclusion chromatography (SEC) using a Varian liquid chromatograph equipped with a UV and refractive index detector. Polymer functionality was verified by oxidation of thiol to disulfide.

Thermal Analysis:

Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T_g) of the sample has been considered.

Solubility:

Polymer is soluble in THF, CHCl₃ and toluene.

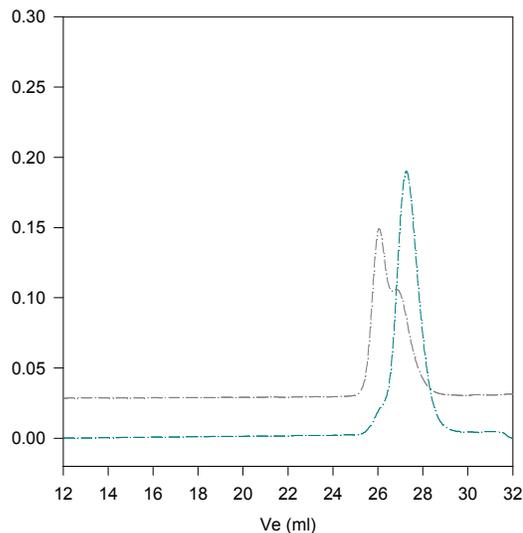SEC of the sample:**P4422-SSH (PSt-CH₂CH(CH₃)SH)**

Size exclusion chromatograph of thiol terminated polystyrene:

- M_n=2500 M_w=2700 PI=1.05 (before termination with propylene sulfide)
- After termination with ethylene sulfide (SH functionality around 60%)
- .-.- after oxidation with iodine, indicating about 60% functionalization

DSC thermogram for the polymer: