


Sample Name:

Poly(methyl methacrylate-*co*(*random*)-*n*-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample #: P10456-MMA*n*BuMA*r*an-*b*-HEMA

Structure:

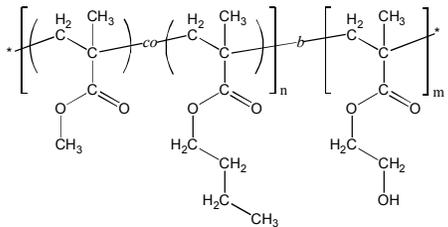

Composition:

$M_n \times 10^3$ (g/mol)	26.5- <i>b</i> -22.0
M_w/M_n	1.18
Molar ratio MMA : nBuMA	50 : 50 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	23 : 32 : 45 (wt%)
T_g (MMA <i>n</i> BuMA)	65 °C
T_g (HEMA)	112 °C

Synthesis Procedure:

Poly([methyl methacrylate-*co*-*n*-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and *n*-butyl methacrylate (*n*-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

Solubility: The polymer is soluble in THF, DMF.


Characterization:

The polymer composition was determined by ¹H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the -OCH₂-protons of nBuMA (at δ = 3.9 ppm) to the integration of methoxy group of MMA (at δ = 3.6 ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of -OCH₂- protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA*n*BuMA) block.


The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA*n*BuMA-*b*-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.

¹H NMR of MMA*n*BuMA*r*an [first block]:

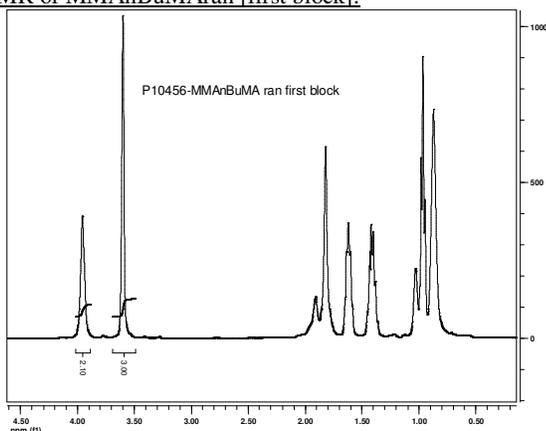


¹H NMR of MMA*n*BuMA*r*an-*b*-HEMA diblock copolymer:

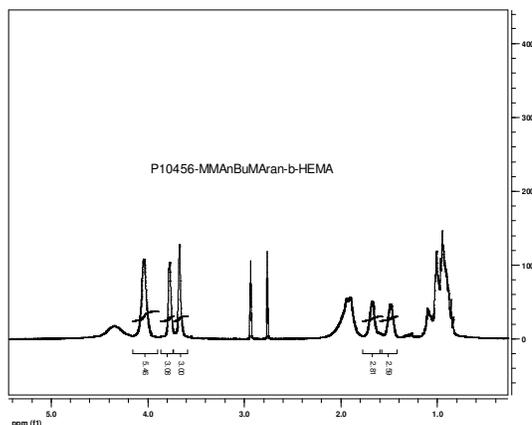


SEC of MMA*n*BuMA*r*an [first block]:

Sample ID: P10456-1

Concentration (mg/mL)	5.0767
Sample dn/dc (mL/g)	0.0800
Method File	PS80K-July-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

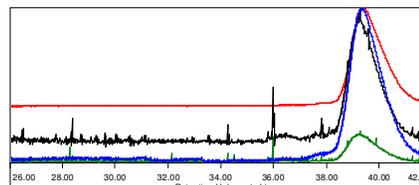


Sample	Mn (Da)	Mw (Da)	Mp (Da)	Mw/Mn	IV (dL/g)
P10456-1_2011-09-30_15:52:16_01.vdt	26,612	28,460	28,636	1.069	0.2406

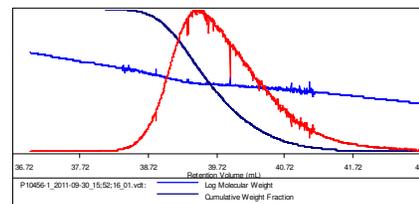

SEC of MMA*n*BuMA*r*an and MMA*n*BuMA*r*an-*b*-HEMATMS:

P10456-MMA*n*BuMA*r*anHEMA

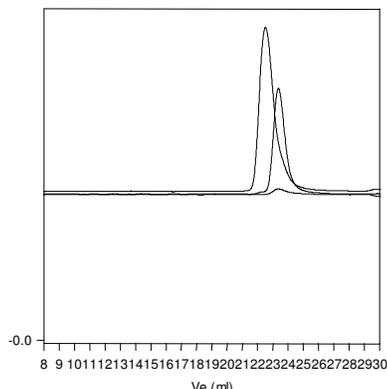

Size exclusion chromatography of
1. Random copolymer of MMA and nBuMA: Mn 26,600 Mw: 28,500 Mw/Mn 1.07
Poly(MMA-*n*BuMA*r*an)-*b*- Poly 2-Hydroxy ethyl methacrylate (Protected with TMS)
Mn 26,500-*b*-34,000 Mw/Mn 1.18
After Deprotection of HEMA TMS : Mn 26,600-*b*-22,000 Mw/Mn 1.18
In THF after deprotection, the SEC profile shows no micellization