


Sample Name:

Poly (ethylene glycol), (α -azide, ω -hydroxy)-terminated

Or azide terminated Polyethylene glycol

Sample #: P5805- EGOHN3

Structure:**Composition:**

$M_n \times 10^3$	PDI
1.6	1.29
Azide functionality by HNMR 50%	

Synthesis Procedure: In this case the initiator was azido ethoxy ethanol:

Azide end functionalized Poly(ethylene glycol)methyl ether is prepared by living anionic polymerization of ethylene oxide, followed by modification of OH terminal to mesylate and than to azide group.

Characterization:


An aliquot of the poly(ethylene oxide) before addition of mestyl chloride was analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The polymer obtained at each step and the final block copolymer composition was calculated from $^1\text{H-NMR}$ spectroscopy.

FTIR:


N3 characteristic appears at 2101 cm^{-1} .

Solubility:

N3 end functionalized Poly(ethylene oxide) is soluble in CHCl_3 , THF and precipitated out from cold ethanol, diethyl ether.

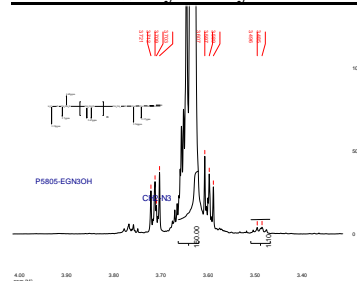 α - azide ω -hydroxy terminated PEG:**SEC of the polymer:**

P5805-EGOHN3

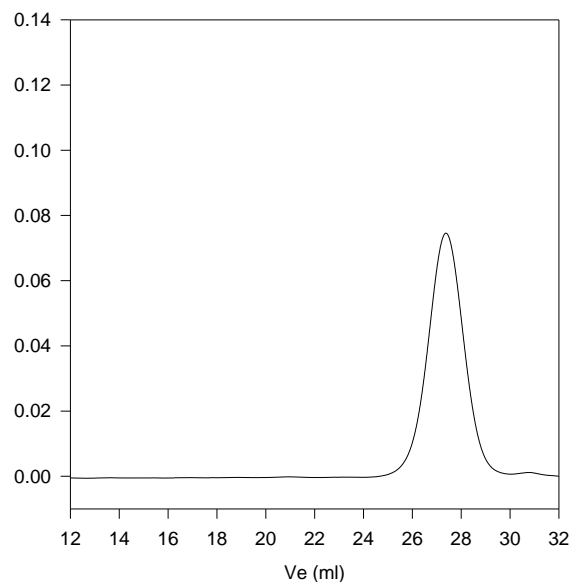

Size Exclusion Chromatography of N3 end functionalized Poly(ethylene glycol)

$M_n = 1600$, $M_w = 2100$, $M_w/M_n = 1.26$