


Sample Name:

Poly(methyl methacrylate-*co*_(random)-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample #: P10545X-MMAAnBuMAran-b-HEMA

Structure:

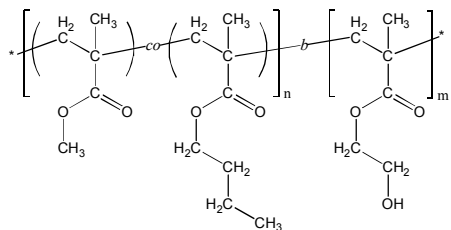

Composition:

$M_n \times 10^3$ (g/mol)	28.0-15.0
M_w/M_n	1.15
Molar ratio MMA : nBuMA	50 : 50 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	27 : 38 : 35 (wt%)
T_g (MMAAnBuMA)	65 °C
T_g (HEMA)	112 °C

Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

Solubility: The polymer is soluble in THF, DMF.

Characterization:


The polymer composition was determined by ^1H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the $-\text{OCH}_2$ -protons of nBuMA (at $\delta = 3.9$ ppm) to the integration of methoxy group of MMA (at $\delta = 3.6$ ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of $-\text{OCH}_2$ - protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMAAnBuMA) block.

The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMAAnBuMA-b-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.


Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.

^1H NMR of MMAAnBuMAran [first block]:

P10545x-MMAAnBuMA ran first block

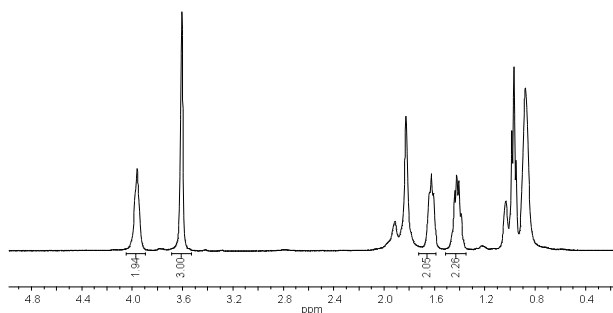


^1H NMR of MMAAnBuMAran-b-HEMA in DMF-d7:

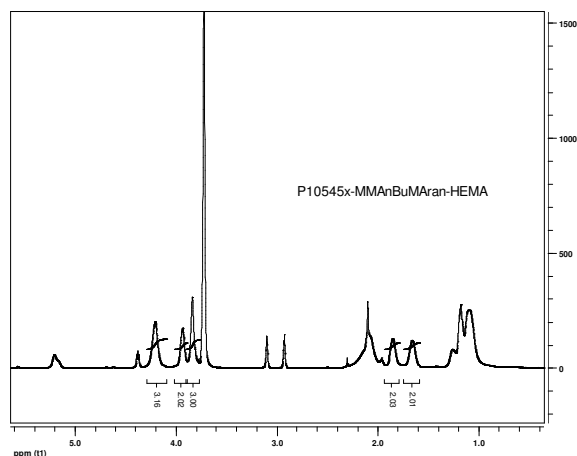


SEC of MMAAnBuMAran [first block]:

Sample ID: P10545-1MMAAnBuMA first block

Concentration (mg/mL)	7.4427
Sample dn/dc (mL/g)	0.0800
Method File	P580K-July-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

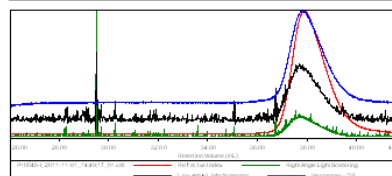


Sample	Mn (Da)	Mw (Da)	Mp (Da)	Mw/Mn	IV (dL/g)
P10546-1_2011-11-01_14:49:17_01.vdt	28,142	30,521	30,264	1.085	0.2515

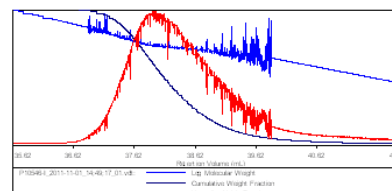

SEC of MMAAnBuMAran and MMAAnBuMAran-b-HEMATMS:

P10545X-MMAAnBuMAran-b-HEMA

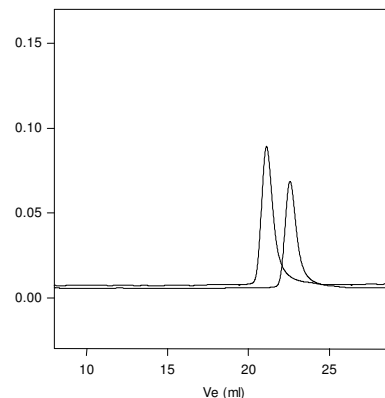

Size exclusion chromatography of
1: Poly MMAAnBuMAran: Mn 28,000 Mw: 30,500 Mw/Mn 1.09
Poly(MMAAnBuMAran)-b- Poly 2-Hydroxy ethyl methacrylate (Protected with TMS)
Mn 28,000-b-23,300 Mw/Mn 1.15
After Deprotection of HEMA TMS : Mn 28,000-b-15,000 Mw/Mn 1.15
The deprotected polymer does not elute in THF.