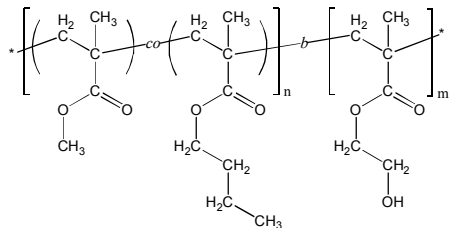


Sample Name:

Poly(methyl methacrylate-*co*_(random)-n-butyl methacrylate)-*block*-poly(2-hydroxyethyl methacrylate)

Sample #: P10610B-MMA_nBuMA_ran-b-HEMA**Structure:****Composition:**

$M_n \times 10^3$ (g/mol)	25.0- <i>b</i> -19.0
M_w/M_n	1.15
Molar ratio MMA : nBuMA	50 : 50 (mol/mol)
Weight ratio MMA:nBuMA:HEMA	24 : 33 : 43 (wt%)
T_g (MMA _n BuMA)	65 °C
T_g (HEMA)	112 °C

Synthesis Procedure:

Poly([methyl methacrylate-*co*-n-butyl methacrylate]-*b*-2-hydroxyethyl methacrylate) block copolymer was synthesized by living anionic polymerization. First, methyl methacrylate (MMA) and n-butyl methacrylate (n-BuMA) were co-polymerized; and then 2-[trimethylsilyloxy]ethyl methacrylate (hydroxyprotected HEMA monomer) was added. The obtained block copolymer was precipitated in acidic methanol solution to deprotect the hydroxyl group.

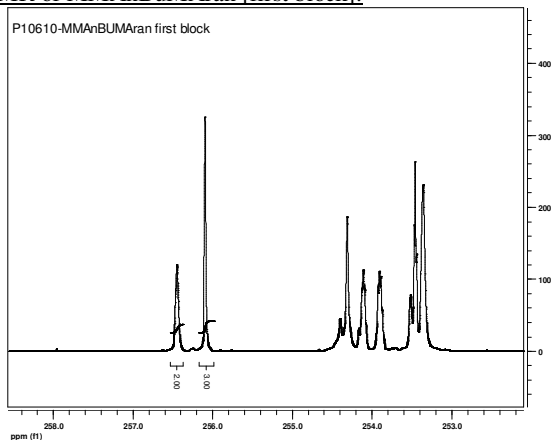
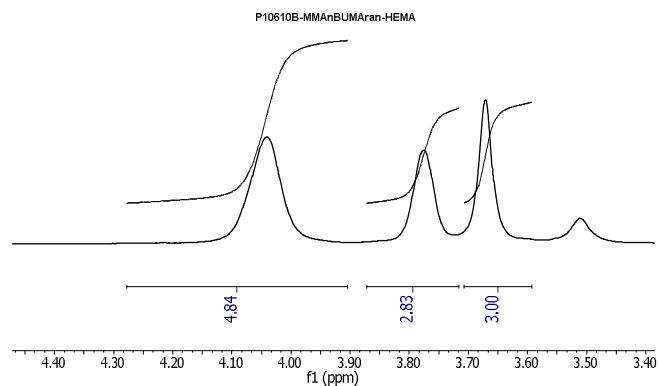
Solubility: The polymer is soluble in THF, DMF.

Characterization:

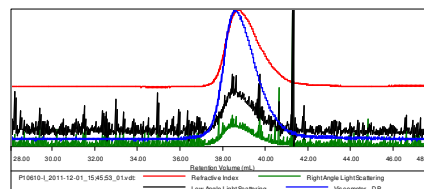
The polymer composition was determined by ¹H NMR. MMA:nBuMA molar ratio was calculated by comparing the integration of the -OCH₂- protons of nBuMA (at δ = 3.9 ppm) to the integration of methoxy group of MMA (at δ = 3.6 ppm). Molecular weight of the second (HEMA) block was calculated by comparing the integration of -OCH₂- protons of HEMATMS to the integration of methoxy group of MMA and using SEC data for the first (MMA_nBuMA) block.

The average molecular weight and polydispersity index were determined by size exclusion chromatography (SEC). For SEC analysis, the MMA_nBuMA-b-HEMA block copolymer can be treated with acetic anhydride in presence of pyridine to convert the hydroxy-groups to acetate groups.

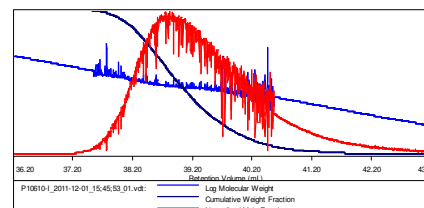
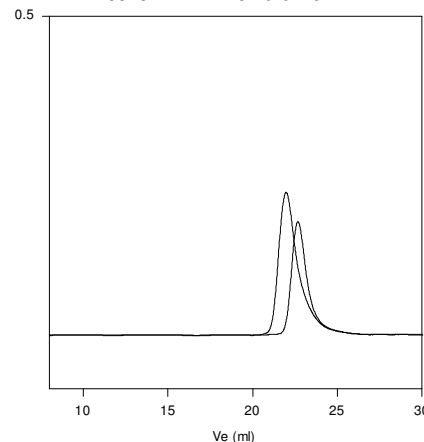
Thermal analysis of the sample was done on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The glass transition temperature (T_g) was determined as a midpoint of step change in heat flow curve for the second heating scan.

¹H NMR of MMA_nBuMA_ran [first block]:**¹H NMR of MMA_nBuMA_ran-b-HEMA diblock copolymer:****SEC of MMA_nBuMA_ran [first block]:**Sample ID: P10610-I-MMA_nBuMA

Concentration (mg/mL)	7.2389
Sample dn/dc (mL/g)	0.0800
Method File	PS80K-Oct-0000.vcm
Column Set	3x PL 1113-6300
System	System 1



Sample	Mn (Da)	Mw (Da)	Mp (Da)	Mw/Mn	IV (dL/g)
P10610-I_2011-12-01_15:45:53_01.vdt	24,991	28,526	27,482	1.141	0.2233

**SEC of MMA_nBuMA_ran and MMA_nBuMA_ran-b-HEMATMS:**P10610B-MMA_nBuMA_ran-b-HEMA

Size exclusion chromatography of
 1. MMA_nBuMA_ran block Mn 25,000 Mw 28,500 Mw/Mn 1.14
 2. MMA_nBuMA_ran-b-HEMATMS: 25,000-29,500 Mw/Mn : 1.15
 After deprotection Mn 25,000-b-19,000 Mw/Mn 1.15